

	Expert on ceramic papers
	Mario Montes Universidad del Pais Vasco mario.montes@ehu.es Expert in structured catalysts for environmental protection
	Luis J Alemany Universidad de Malaga luijo@uma.es Expert in abatement of diesel exhaust pollutants
Opposed Reviewers:	
Additional Information:	
Question	Response
§Are you submitting to a Special Issue?	No

Novel ceramic paper structures for diesel exhaust purification

Sabrina A. Leonardi¹, Fernando E. Tuler¹, Eric M. Gaigneaux², Damien P. Debecker^{2,*},
Eduardo E. Miró¹, Viviana G. Milt^{1,*}

¹*Instituto de Investigaciones en Catálisis y Petroquímica, INCAPE, Universidad Nacional del Litoral, CONICET, Facultad de Ingeniería Química, Santiago del Estero, 2829-3000, Santa Fe, Argentina.*
²*Institute of Condensed Matter and Nanosciences – MOlecules, Solids and reactiviTy (IMCN/MOST), Université catholique de Louvain, Place Louis Pasteur 1 box L4.01.09, 1348 Louvain-La-Neuve, Belgium.*

*corresponding authors: vmilt@fiq.unl.edu.ar (V.G. Milt), damien.debecker@uclouvain.be (D.P. Debecker)

Abstract

The catalytic combustion of diesel soot is addressed with flexible and structured “paper catalysts”. Two different series of catalysts were prepared either by drip impregnation or by a spray method to deposit a mixture of Co, Ba, and K or a mixture of Co and Ce onto SiO₂-Al₂O₃ ceramic paper matrixes. In every case CeO₂ nanoparticles were added to bind the ceramic fibers. SEM images showed that the impregnation method generated catalytic particles concentrated as large chunks (> 10 μm), mainly at ceramic fiber crossings, whereas the spray method produced smaller catalytic particles (< 1 μm) well distributed throughout the ceramic paper. Besides, Co-Ba-K particles appeared better dispersed on the surface of ceramic fibers than Co-Ce due to the presence of K. Additionally, FTIR spectra showed the formation of O₂²⁻ and O₂⁻ species associated with CeO₂ (binder) on the samples containing potassium which gave the Co-Ba-K-ceramic paper good catalytic properties, thus making the Co-Ba-K drop impregnated the best catalyst both considering activity and stability.

Successive temperature programmed oxidation (TPO) runs up to 700°C caused the formation of cobalt silicates in the catalytic ceramic paper prepared by the spray method, as indicated by TPR. The formation of these species was probably favored by the smaller size of cobalt particulates and their higher dispersion in the catalysts prepared by the spray method. This provoked the partial loss of the redox properties of Co₃O₄. TPR experiments also indicated the formation of BaCoO₃ in Ba-containing ceramic paper, which could help in maintaining the catalyst activity after several TPO runs through the capacity of this mixed perovskite-type oxide to trap and release NO_x.

1
2
3
4
5
6
7 **Keywords**
8

9 Cobalt, Barium, Potassium; Cerium; catalytic ceramic paper; structured catalysts; diesel
10 soot combustion; spray deposition.
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1. Introduction

During the last decade fiber materials have gained in popularity for catalytic applications due to the benefits associated with the high surface to volume ratio and the high void fractions offered by these structures. Based on the preparation method the fibrous substrates can be fitted to various geometries. Also they exhibit lower costs and a better coatability compared to microchannel reactors. The variety of different fiber based catalyst supports is large and each type of support shows its own advantages, as a function of the chosen fiber material and manufacturing process [Reichelt et al. 2014]. An interesting possibility is to shape the fibers as papers that can be easily rolled-up inside cartridges that, for example, can be useful to develop catalytic filters for the abatement of diesel soot particles. The development of new and more efficient processes for the abatement of diesel contaminants has renewed its public concern since the classification by the World Health Organization of the soot particles as carcinogenic grade 1 and also since the recent Volkswagen scandal.

Nowadays, commercialized filters consist of SiC monoliths with active elements on it [Quiles-Díaz et al. 2015; Aneggi et al. 2014; Liu et al. 2015; Tuler et al. 2015a]. As an alternative, our group proposed to use the mentioned ceramic papers as suitable materials to conform flexible structured catalysts and diesel filters [Tuler et al. 2014; Koga et al. 2008; Ishihara et al. 2010; Koga et al. 2006; Koga et al. 2008; Koga et al. 2009]. Ceramic papers present suitable mechanical properties to resist assays from a test bench in which they were placed inside a metal housing, at the exhaust pipe outlet of a Corsa 1.7 diesel vehicle [Tuler et al. 2014]. Optimal mechanical properties were obtained through the incorporation of a suspension of CeO₂ nanoparticles as a binder (10 or 20 wt. % CeO₂) during the

papermaking process. The passive regeneration of the filter however requires the addition of catalytic components [Piumetti et al. 2016].

In this work we present a systematic study performed with the aim of preparing active and stable catalytic filters for the abatement of diesel soot particulates. These filters are prepared from $\text{SiO}_2\text{-Al}_2\text{O}_3$ ceramic fibers arranged under the form of papers discs using the papermaking process. These papers have been useful to trap soot particles from the exhausts of a real diesel engine [Tuler et al. 2014]. In order to continuously regenerate the filters, a catalytic phase must be firmly attached to the ceramic fibers and, at the same time, the catalytic particles should be highly dispersed throughout the paper and small enough to be catalytically efficient to burn the soot under working conditions. To this end, in this work we explore two methods for the incorporation of the catalytic particles: drip impregnation and spray deposition. The first method involves the impregnation by dripping a solution of precursor salts containing the desired catalytic components directly on the paper support, followed by calcination. The second one is inspired by the aerosol process [Tuler et al. 2015b], which is currently emerging as a powerful tool for the preparation of advanced materials, especially catalysts [Colbeau-Justin et al. 2014; Debecker et al. 2012; Debecker et al. 2014; Maksasithorn et al. 2015; Pega et al. 2009]. We chose two active formulations that have already proved to be active in previous works but having different catalytic properties: Co-Ba-K and Co-Ce [Tuler et al. 2015a and b]. The first formulation takes advantage of the redox capacity of cobalt oxide that is enhanced by the high availability of surface oxygen species of ceria. The second one also features the high oxidative potential of cobalt but additionally incorporates the capacity of Ba and K to form nitrate species which are known to be also active for soot oxidation [Zhang et al. 2018]. Also, K is known to allow increasing the soot-to-catalyst interaction. The prepared

structured catalysts were evaluated for soot combustion (temperature programmed oxidation TPO experiments) in terms of the activity characterized by the maximum combustion rate temperature, and stability during successive TPO runs. In order to correlate the catalytic measurements with physical chemistry properties, both fresh and used catalysts were characterized by TPR, XRD, SEM and FTIR.

2. Experimental

2.1. Ceramic paper preparation

Following a procedure previously in detail described [Tuler et al. 2014] ceramic paper discs (16.5 cm in diameter) were prepared from ceramic fibers ($\text{SiO}_2\text{-Al}_2\text{O}_3$), which were dispersed in an aqueous medium where also a binder was added (20 wt.% of CeO_2 nanoparticles, Nyacol). Cellulose fibers were also incorporated to enhance the retention of the ceramic fibers during the mat formation, along with cationic and anionic polymers: polyvinylamine (PVAm) and anionic polyacrylamide (A-PAM), respectively.

A two-step method was employed for the preparation of catalytic ceramic papers. In the first step, following the papermaking technique, a sheet was formed and dried under controlled atmosphere (23°C, 50% R.H.) for 24 h and finally calcined in air at 600°C for 2 h. The second step corresponded to the deposition of the catalytic ingredients. Two series of catalysts were prepared, one adding Co, Ba and K and the other incorporating Co and Ce from their corresponding nitrate solutions as will be explained below. It must be pointed out that Ce oxide (Nyacol) was also incorporated as a binder in both formulations, which mainly accumulates as patches of about 5 μm in the fiber crossings due to capillary forces exerted during the drying step. Thus, both formulations (Co-Ba-K and Co-Ce) contain

CeO₂ as the binder. Two methods were used to incorporate the catalytic components: the conventional dripping method and the spray technique.

2.2. Drip impregnation

Co-Ce-catalytic ceramic paper

The incorporation of the catalytic ingredients by drip impregnation was carried out using a solution of Ce(NO₃)₃ and Co(NO₃)₂, which was prepared by dissolving the necessary amount of each precursor salt in the volume of water calculated to saturate the paper structure, so as to load 4 wt.% of Ce(NO₃)₃+Co(NO₃)₂ (weight ratio Ce:Co = 2.37:1). The impregnated ceramic paper discs were then dried at room temperature overnight and calcined in a furnace at 600 °C for 2 h. The catalysts were denoted as Co-Ce-I.

Co-Ba-K-catalytic ceramic paper

The incorporation of the catalytic ingredients by drip impregnation was carried out using a solution of Ba(CH₃COO)₂, KNO₃ and Co(NO₃)₂ (weight ratio Ba:K:Co = 1.33:0.58:1), which was prepared by dissolving the necessary amount of each precursor salt in the volume of water calculated to saturate the paper structure, so as to load 5 wt.% of catalyst (expressed as Co + Ba + K per gram of ceramic fiber). The impregnated ceramic paper discs were then dried at room temperature overnight and calcined in a furnace at 600°C for 2 h. The catalysts were denoted as Co-Ba-K-I.

2.3. Spray deposition

Co-Ce-catalytic ceramic paper

In the second case (Fig 1), a mixed solution of Ce(NO₃)₃ (0.622 g/l) and Co(NO₃)₂ (0.556 g/l) was placed in an atomizer (6-Jet 9306A atomizer from TSI) and sprayed with an air pressure of 30 psi. The aerosol was partially dried by quickly passing through a tubular

furnace heated at 400°C (residence time of about 1 second) and then the particles were directly sprayed onto the ceramic papers. Any excess particles exiting across the paper were retained by an absolute filter. The spraying time (6-8 h) were adjusted in order to load 4 wt.% Ce(NO₃)₃+Co(NO₃)₂ on the ceramic paper discs. The sprayed ceramic papers were then calcined in a furnace at 600°C for 2 h. The actual loading was verified by weighing. Catalytic papers are denoted as Co-Ce-S.

Co-Ba-K-catalytic ceramic paper

Similarly, as previously described, a mixed solution containing 0.056 g/ml Ba(CH₃COO)₂, 0.111 g/ml Co(NO₃)₂ and 0.034 g/ml KNO₃ was placed in the atomizer (6-Jet 9306A atomizer from TSI), the aerosol produced was passed through a tubular furnace set at 400°C and the particles were sprayed onto the ceramic paper discs. After 6 h of spraying, 4.4 wt.% of active species were loaded on the ceramic paper pieces. Finally, the sprayed ceramic discs were calcined at 600°C for 2 h. Thus obtained, catalytic papers were denoted as Co-Ba-K-S.

2.4. Characterization

Crystalline phases were determined with a Shimadzu XD-D1 instrument with monochromator using CuK α radiation at a scan rate of 2 °/min, from 2 θ = 15 ° to 80 °. The pieces of about 16 mm in diameter were supported in a special sample holder designed for the XRD analysis. The software package of the equipment was used for the phase identification from the X-ray diffractograms.

Microscopic images were obtained with a SEM Jeol JSM-35C equipment was employed operated at 20 kV acceleration voltage. Samples were glued to the sample holder with Ag painting and then coated with a thin layer of Au in order to improve the images.

1
2
3
4 Fourier Transform Infrared Spectroscopy (FTIR) was used to identify the
5 functional groups. Samples were prepared in the form of pressed wafers (ca. 1%
6 sample in KBr). A Shimadzu IR Prestige-21 spectrometer was utilized to obtain the
7 infrared spectra. All spectra involved the accumulation of 40 scans at 8 cm⁻¹
8 resolution.
9

10
11 The elemental chemical analysis was performed by EDS using an energy dispersive
12 instrument – Phenom model Word ProX (Netherlands) – operated at 15 kV of acceleration
13 voltage, on several zones of the samples. Also, the mapping of bigger areas was carried out.
14 Semi quantitative results were obtained with the theoretical quantitative method (SEMIQ),
15 which does not require standards.
16

17
18 Temperature-Programmed Reduction (TPR) was used to study the reducibility of
19 the catalysts. The experiments were run on a Micromeritics Autochem II instrument with a
20 TCD detector. The reducing gas flow was 5% H₂ in Ar, heating the samples from room
21 temperature to 1000°C at a heating rate of 10°C min⁻¹.
22

23 24 2.5. Soot combustion experiments (Temperature Programmed Oxidation)

25
26 Soot particles were produced by burning a commercial diesel fuel (YPF, Argentina)
27 in a glass vessel. After being collected from the vessel walls, the soot was dried in a stove
28 at 120°C for 24 h. Soot particles were dispersed in n-hexane using an ultrasonic bath in
29 order to obtain a homogeneous suspension of 600 ppm of diesel soot in n-hexane. The
30 incorporation of soot particles to the ceramic paper pieces (1.6 cm in diameter discs) was
31 carried out by adding the suspension dropwise until saturation, and then drying at room
32 temperature.
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

The catalytic activity of the ceramic papers for the soot combustion was studied by Temperature Programmed Oxidation (TPO). For this purpose, the structured samples loaded with the soot were heated at 5°C/min from room temperature up to 600°C in O₂ (18%)+NO (0.1%) diluted in He (total flow 20 ml/min) in a flow equipment designed for this purpose. The exhaust gases were analyzed with a Shimadzu GC-2014 chromatograph (with TCD detector). In order to evaluate the stability of the systems, five successive cycles were performed, the first two up to 600°C and the following three up to 700°C. Between each cycle, the catalytic ceramic disc was removed from the set-up and soot was incorporated into the sample as previously described. After the five cycles, samples were characterized, and named as stated in 2.3, with an asterisk.

3. Results and discussion

In a previous work [Tuler et al. 2015b] we prepared catalytic ceramic paper by the spray method adding two catalytic components, cobalt and cerium. We demonstrated the efficiency of this method to homogeneously disperse small catalytic particles on ceramic fibers. The structured catalysts thus obtained burnt soot with a maximum in the TPO profiles at about 400°C. To further study this system, successive TPO runs were carried out to check catalytic stability. But also, and with the aim of enhancing catalytic activity, other components were added as catalytic ingredients: cobalt, barium and potassium, the last two aim at trapping NO_x and favoring the soot-to-catalyst contact, respectively. A series of experiments in parallel was carried out adding the catalysts to the ceramic paper either by the spray method or using the more traditional impregnation one.

3.1. Scanning Electron Microscopy and Energy Dispersive X-ray Spectroscopy

SEM images (Fig 1) show that ceramic paper is an open structure formed by a matrix of ceramic fiber, where catalytic particles appear distributed along the fibers. As previously seen [Tuler et al. 2015b], the sample prepared by the impregnation method containing cobalt and cerium, Co-Ce-I, exhibits catalytic particles concentrated as large chunks ($> 10 \mu\text{m}$) heterogeneously distributed along the fibers, and deposited in the fiber crossings where the binder is mainly accumulated. (Fig 1a), whereas the spray method produced smaller catalytic particles ($< 1 \mu\text{m}$, Fig 1b) well distributed throughout the ceramic paper (Co-Ce-S). No significant differences were observed in the case of Co-Ba-K-containing ceramic paper, compared to Co-Ce ones. The traditional impregnation method (Fig 1 c and e) produces larger particles than the spray one (Fig 1 d and f).

The catalytic component distribution was studied by EDS analysis (mapping). Figure 2 shows images obtained for impregnated and sprayed samples. Although as said before the distribution of particles is different in the catalytic papers obtained using both methods, in the case of Co-Ba-K samples (both Co-Ba-K-I and Co-Ba-K-S) catalytic components (Co, Ba and K) appear well distributed all along the structure covering the ceramic fibers and forming catalytic agglomerates, which is not the case of both Co-Ce samples (Co-Ce-I and Co-Ce-S), where ceramic fibers appear to be mainly uncovered, and only the catalytic chunks are clearly observed. The better coverage in the samples containing K is most probably due from the formation of potassium salts and oxides of low melting point, favoring the distribution of catalytic components all along ceramic fibers.

3.2. Infrared Spectroscopy (FTIR)

Figure 3a shows FTIR spectra of catalytic ceramic papers, where the spectrum of bare ceramic fibers is also included for comparison. This last exhibits a broad band at 1000

-1200 cm⁻¹ due to Si-O stretching of SiO₂ ceramic fibres, which also appears in the spectra of the catalytic ceramic papers. Besides, all spectra exhibit the signal at 667 cm⁻¹, associated to Co-O stretching of Co²⁺ in the Co₃O₄ spinel [Khalaji et al. 2014]. No other defined signals could be ascribed in the IR spectra of Co-Ce-containing ceramic paper whereas for Ba,Co,K-containing samples, small signals at 1069, 1110 and 1180 cm⁻¹ appear. These peaks correspond to peroxide (O₂²⁻) or superoxide (O₂⁻) species associated to CeO₂ and preferentially formed in the presence of K. K indeed incorporates into the CeO₂ lattice and generates anionic vacancies increasing the number of peroxide and superoxide species [Gross et al. 2012; Kaplin et al. 2017].

3.3. Temperature-Programmed Reduction (TPR)

The reducibility of the catalytic ceramic papers was studied by TPR (Fig 3b). Co-Ce-containing catalysts show different profiles according to the preparation protocol. The TPR profile corresponding to Co-Ce-I could be convoluted considering six peaks with different intensities (very strong, vs; medium, m; and weak, w), with maxima at 355 (vs), 400 (m), 442 (vs), 480 (m), 686 (w) and 758°C (m) (Fig 2S). The overlapped peaks at 355 and 442°C correspond to Co₃O₄ reduction (Co³⁺→Co²⁺ and Co²⁺→Co⁰, respectively); the peak with a maximum at 400°C corresponds to CeO₂ (surface) reduction, which is reported to occur between 290 and 465°C [Jin et al. 2016; Gómez et al. 2016], whereas the peak at 480°C (tailoring) could be associated to a wide distribution of sizes of cobalt particles. The signal with maximum at 686°C could be ascribed to the CoAl₂O₄ spinel reduction to Co⁰ and the peak at 758°C could be associated with bulk CeO₂ reduction [Liotta et al. 2006; Han et al. 2015]. In the case of Co-Ce-S, the corresponding TPR profile is similar to that of Co-Ce-I and it was fitted considering five reduction peaks, with maxima at 359 (w), 445 (vs), 483 (m), 688 (m) and 758°C (m) (Fig 2S). The main difference between the

1
2
3
4 impregnated and the sprayed samples appears in the 320-480°C region, associated with
5
6 Co₃O₄ reduction. According to Tarka et al. (2017) [Potoczna-Petru et al. 2001], smaller
7
8 Co₃O₄ particles are harder to reduce and the spray method favors the formation of smaller
9
10 particles (SEM images, Fig 1). Besides, CeO₂ promotes Co₃O₄ dispersion, favoring the
11
12 formation of smaller crystallites. This explains why the sprayed sample exhibits lower
13
14 intensity peaks in the 320-480°C zone and a bigger one at 483°C [Luo et al. 2008].
15
16
17

18
19 TPR profiles of Co-Ba-K-containing catalysts are more complex (Fig 3) and the
20
21 corresponding fittings are shown in (Fig 3S). In the case of Co-Ba-K-I, the peaks at 305 (m)
22
23 and 354°C (s) correspond to Co₃O₄ reduction that occurs at lower temperatures if compared
24
25 to Co-Ce-containing catalysts probably due to the higher accessibility of H₂ to cobalt
26
27 particles originated by the presence of K, which enhanced catalyst dispersion (as seen by
28
29 EDS). At 404°C, a very strong signal is observed, which, according to previous works [Milt
30
31 et al. 2005; Xu et al. 2016], could correspond to BaCoO_{3-y} perovskite-type oxide reduction.
32
33 The shoulder at 473°C (m) could correspond, as previously described, to cobalt reduction at
34
35 the interface Co₃O₄ - CeO₂ (Co²⁺→Co⁰), associated to the presence of different sizes of
36
37 cobalt particles. The two overlapped signals with maxima at about 545 (s) and 614°C (m)
38
39 could be associated to KNO₃ reduction [Mosconi et al. 2007], whereas at higher
40
41 temperatures (ca. 780°C), the wide and intense peak could involve CoAl₂O₄ along with
42
43 bulk CeO₂ reduction. If compared with Co-Ce-catalysts, this high temperature peak is
44
45 considerably higher in the Ba-containing samples and appears at slightly higher
46
47 temperatures. A similar effect was observed by Marrero-Jerez et al. [Marrero-Jerez et al.
48
49 2014] when studying gadolinia-doped CeO₂ supported on Al₂O₃: the increase in Gd content
50
51 resulted in a shift towards higher temperatures of the peak associated to bulk Ce⁺⁴ reduction
52
53
54
55
56
57
58
59
60
61
62
63
64
65

and also, in an increment in the area beneath the TPR peak. Also, the reduction of the BaCeO₃ perovskite should be considered [Yang et al. 2010].

In the case of the sprayed sample (Co-Ba-K-S), the TPR profile is similar to that of Co-Ba-K-I, the main differences being the much less intense peak at 402°C and the absence of the peak at 475°C, as previously discussed, associated with the presence of the BaCoO_{3-y} perovskite-type oxide and with the different sizes of cobalt particles, respectively. Probably, the traditional impregnation method favors the BaCoO_{3-y} perovskite formation whereas in the spray method, the partial drying of aerosol droplets when they pass through the furnace at 400°C produces more homogeneous sizes of particles. Besides, as previously described, smaller Co₃O₄ particles are more difficult to reduce. On the other hand, the bigger peak at 780°C should correspond to BaCO₃ reduction, present in higher amounts in the sprayed sample (Co-Ba-K-S), along with BaCeO₃ reduction.

3.4. X-ray Diffraction (XRD)

Figure 4 shows XRD patterns. Both Co-Ce-S and Co-Ce-I show signals corresponding to the CeO₂ fluorite-type oxide (JCPDS # 34-394). No signals associated with cobalt species appear, indicating their high dispersion (small particle size). However, if considering the cobalt percentage in the catalyst (12 wt. %) and the amount of catalyst loaded on the ceramic paper (5 wt.%), it is probably that the cobalt content is close to the detection limit of the technique. In the case of Co-Ba-K-containing ceramic papers, the XRD pattern of the impregnated sample (Co-Ba-K-I) shows, besides CeO₂ signals, others associated to BaCO₃ (JCPDS # 45-1471). The sprayed sample (Co-Ba-K-S) also show the BaCO₃ signals, but with a much lower intensity, accounting for a higher dispersion of BaCO₃ particles (Fig 1).

3.5. Catalytic evaluation (TPO) – Stability runs

1
2
3
4 In a previous work [Tuler et al. 2015b] we observed that the incorporation of cobalt
5 and cerium by the spray technique (Co-Ce-S catalyst) resulted in a more active catalyst than
6 that prepared by the traditional impregnation technique (Co-Ce-I catalyst). However,
7 stability is as important as activity, and unfortunately, the structured catalysts prepared by
8 the spray technique did not behave well in cycling experiments. Thus, in this work the
9 stability of the drip impregnation and spray-made catalysts was further studied.
10
11
12
13
14
15
16
17

18 The two first TPO runs for Co-Ce-I up to 600°C indicated that no deactivation was
19 observed (Fig 5a). Nevertheless, after the three successive TPO runs up to 700°C, a partial
20 deactivation of the catalysts occurred, as observed by the shift in the TPO profiles to higher
21 temperatures. The temperature of maximum reaction rate indicated that after the five TPO
22 runs, T_M values shifted from 480°C to 540°C (Table 1). The sprayed sample (Co-Ce-S) was
23 initially more active with a T_M value of 453°C for the first run and started to deactivate
24 already after the first TPO run (Fig 5a). Then T_M values progressively shift down to 530°C
25 for the fifth run, i.e. still slightly better than Co-Ce-I (Fig 5a and Table 1).
26
27
28
29
30
31
32
33
34
35
36
37

38 Co-Ba-K-containing ceramic papers were more active and stable if compared with
39 those containing cobalt and cerium. For Co-Ba-K-S, the temperature of maximum
40 combustion rate of the first run was as low as 390°C and after a slight deactivation in the
41 first two cycles, the T_M was maintained around 428°C in the next three cycles (Fig 5b and
42 Table 1). However, the impregnated ceramic paper (Co-Ba-K-I) performed even better,
43 both considering activity and stability. In fact, a T_M of 390°C was maintained from the first
44 to the fifth TPO run.
45
46
47
48
49
50
51
52
53
54

55 As Figure 6 summarizes, there is a marked difference in the catalytic activity of the
56 systems containing either Co-Ce or Co-Ba-K, the latter being more active. For these
57 catalysts, it is important to note the beneficial effect of NO in the gas phase, which
58
59
60
61
62
63
64
65

1
2
3
4 catalyzes soot combustion from the NO – NO₂ redox cycle, and the presence of KNO₃,
5
6 which favors soot to catalyst contact owing to its low fusion temperature and also provides
7
8 additional active sites [Gross et al. 2009]. Besides, peroxide and superoxide species
9
10 (detected by FTIR), preferentially formed in the presence of potassium, enhance soot
11
12 burning abilities of Co-Ba-K-the catalysts. Remarkably, the Co-Ba-K-I catalytic ceramic
13
14 paper showed a very good activity and stability. In fact, the T_M value is close to the
15
16 temperature of diesel exhaust gases, which potentiates the applicability of this system.
17
18
19
20

21 *3.6. Catalyst characterization after stability runs*

22

23
24 SEM images of catalytic ceramic papers after stability runs (Fig 7) show no
25
26 significant differences if compared with images of fresh samples (Fig 1): big catalytic
27
28 aggregates (> 10 μm) are present on impregnated samples (Co-Ce-I* and Co-Ba-K-I*),
29
30 whereas for sprayed samples, smaller aggregates of catalyst (< 1 μm) are observed after the
31
32 successive TPO runs (Co-Ce-S* and Co-Ba-K-S*). Besides, EDS mapping (Fig 2S,
33
34 Supplementary Information) shows no changes in the catalytic species distribution before
35
36 and after the stability run, which implies the good anchoring of catalytic species deposited
37
38 from both methods. It is worth mentioning that catalytic particles are incorporated partially
39
40 dried when applying the spray method ensuring particle anchoring.
41
42
43
44
45

46
47 In order to elucidate why do some catalytic ceramic papers deactivate and why Co-
48
49 Ba-K-I did maintain its good performance, FTIR and TPR techniques were used. FTIR
50
51 spectra shown in Figure 8a show that all catalysts exhibit the bands at 667 and 565 cm⁻¹
52
53 associated with the Co-O bond stretching of Co₃O₄, appearing better defined for Co-Ba-K-
54
55 I*, and although these signals were better observed for Co-Ce-I (Fig 3a), their intensities
56
57
58
59
60
61
62
63
64
65

decreased after the stability runs. This is probably linked to the catalytic stability of Co-Ba-K-I.

Additionally, TPR studies help understanding this behavior (Fig 8b and the corresponding convolutions in the Supplementary Information Section). Figure 2S compares TPR profiles of catalysts impregnated with cobalt and cerium before and after the stability runs (i.e., Co-Ce-I and Co-Ce-I*). The main difference between both TPR profiles is the almost complete disappearance of the lowest temperature reduction peak, associated to $\text{Co}^{3+} \rightarrow \text{Co}^{2+}$ in Co_3O_4 , in agreement with FTIR. Also, the wide peak at higher temperatures increases for the evaluated sample. This peak was convoluted considering two peaks with maxima at 680 and 750°C respectively, the first one corresponding to the reduction of Co^{2+} in CoAl_2O_4 spinel into Co^0 and the last one, to the reduction of bulk CeO_2 . The formation of the CoAl_2O_4 spinel from Co_3O_4 appears as the main cause of Co-Ce-I deactivation.

In the case of the sprayed sample, the TPR profiles of Co-Ce-S and Co-Ce-S* are similar, although some differences appear at high temperatures: the maximum of the wide peak is shifted from 758 to 780°C and it can be convoluted from three contributions with maxima at 690, 780 and 890°C. The signal with maximum at 690°C, as previously discussed, could be associated to the CoAl_2O_4 spinel reduction and the peak at 780°C, to bulk CeO_2 reduction. The shift from 758 to 780°C could be related to a stronger interaction between Ce and Al, favored from the excursions up to 700°C during the stability runs, probably causing the formation of a binary Ce-Al mixed oxide. The peak with maximum at 890°C could be assigned to cobalt silicate, formed due to small particles of cobalt strongly interacting with silica fibers [Ernst et al. 1999; Santos et al. 2012].

On the other hand, the TPR profile of Co-Ba-K-I* shows no significant differences before and after stability runs. Reduction peaks associated to Co_3O_4 and BaCoO_{3-y} appear at temperatures below 410°C , although the peak corresponding to $\text{Co}^{2+} \rightarrow \text{Co}^0$ appears completely overlapped to that corresponding to the perovskite BaCoO_{3-y} reduction. The shoulder observed at 473°C associated to the reduction of cobalt particles of different sizes appears as a separated peak after the catalytic evaluation whereas the peak caused by the reaction of BaCoO_{3-y} appears a bit less intense. Probably, the ability of BaCoO_{3-y} to reversibly trap and release NO_x [Milt et al. 2005] helps maintaining the catalyst activity. Besides, it can be noticed that the only catalyst that shows a very low temperature reduction peak, close to 250°C , both before and after stability tests, is Co-Ba-K-I, which does not deactivate after stability runs. It is also important to remark that the wide peak, convoluted from two ones with maxima at 545 and 614°C , is observed almost without any difference both before and after activity runs, which discards the occurrence of a potassium loss. These results agree with the fact that maximum combustion rate temperatures keep almost constant (ca. 390°C , Fig 6).

The TPR profile of Co-Ba-K-S* is similar to that of the impregnated catalyst (Co-Ba-K-S), although the relative intensity of species more difficult to reduce vary. Besides, the high temperature reduction peak at ca. 900°C could be related to cobalt silicate formation, which may cause the catalyst deactivation after the third reaction cycle (Figs 5 and 6). The better distribution of cobalt particles obtained by spray would favor cobalt silicate formation, since its corresponding reduction peak appears after stability runs of both samples prepared by the spray method.

Conclusions

1
2
3
4 Co-Ba-K and Co-Ce catalysts deposited on ceramic paper either by drip
5
6 impregnation or by the spray method were prepared and tested for soot combustion. Co-Ba-
7
8 K resulted more active than Co-Ce for both preparation methods and Co-Ba-K drip
9
10 impregnated was the best catalyst both in terms of activity and stability.
11
12

13
14 While Co-Ba-K particulates appeared well dispersed on the surface of ceramic
15
16 fibers, this was not the case for Co-Ce. We attribute this to the presence of K in the former,
17
18 probably responsible for the formation of mobile species during calcination. Besides, FTIR
19
20 characterization showed the formation of peroxide and superoxide species associated to
21
22 CeO₂ and preferentially formed in the samples containing potassium, most probably due to
23
24 the formation of oxygen vacancies into the ceria lattice.
25
26

27
28 Successive runs up to 700°C caused the formation of cobalt silicates in the catalytic
29
30 ceramic papers prepared by the spray method, whose formation is favored for the smaller
31
32 size of cobalt particulates and their higher dispersion specifically obtained via this
33
34 preparation method. Consequently, the redox properties of Co₃O₄ are partially lost when
35
36 these silicates form.
37
38

39
40 TPR experiments indicated the formation of BaCoO₃, which has a reduction peak at
41
42 400°C, in Ba-containing ceramic papers. The capacity of this mixed perovskite-type oxide
43
44 to trap and release NO_x could help in maintaining the catalyst activity after several TPO
45
46 runs. Indeed, the T_M value is close to the temperature of diesel exhaust gases, which
47
48 potentiates the applicability of this system.
49
50
51

52 53 54 55 **Acknowledgements**

56
57 The authors acknowledge the financial support received from ANPCyT, CONICET,
58
59 SECTEI Santa Fe and UNL (Argentina) and Program for Scientific and Technological
60
61
62
63
64
65

Cooperation between the Ministry of Science, Technology and Productive Innovation of Argentina (MINCyT) and the Fonds de la Recherche Scientifique (FNRS) of the French Community of Belgium, BE/12/02.

References

Aneggi E, Wiater D, de Leitenburg C, Llorca J, Trovarelli A (2014) Shape-dependent activity of ceria in soot combustion, *ACS Catal.* 4:172–181.

Colbeau-Justin F, Boissière C, Chaumonnot A, Bonduelle A, Sanchez C (2014) Aerosol route to highly efficient (Co) Mo/SiO₂ mesoporous catalysts, *Adv. Funct.Mater.* 24:233–239.

Debecker DP, Stoyanova M, Colbeau-Justin F, Rodemerck U, Boissière C, Gaigneaux EM, Sanchez C (2012) One-Pot Aerosol Route to MoO₃-SiO₂-Al₂O₃ Catalysts with Ordered Super Microporosity and High Olefin Metathesis Activity, *Angew. Chem. Int. Ed.* 15:2129–2131.

Debecker DP, Stoyanova M, Rodemerck U, Colbeau-Justin F, Boissière C, Chaumonnot A, Bonduelle A, Sanchez C (2014) Aerosol route to nanostructured WO₃-SiO₂-Al₂O₃ metathesis catalysts: Toward higher propene yield, *Appl. Catal. A: General* 470:458–466.

Ernst B, Libs S, Chaumette P, Kiennemann A (1999) Preparation and characterization of Fischer–Tropsch active Co/SiO₂ catalysts, *Appl. Catal. A: General* 186:145–168.

Gómez LE, Múnera JF, Sollier BM, Miró EE, Boix AV (2016) Raman in situ characterization of the species present in Co/CeO₂ and Co/ZrO₂ catalysts during the COPrOx reaction, *Int. J. Hydrogen Energy* 41:4993–5002.

Gross MS, Ulla MA, Querini CA (2009) Catalytic oxidation of diesel soot: New characterization and kinetic evidence related to the reaction mechanism on K/CeO₂ catalyst, Appl. Catal. A: General 360:81–88.

Gross MS, Ulla MA, Querini CA (2012) Diesel particulate matter combustion with CeO₂ as catalyst. Part I: System characterization and reaction mechanism, J. Mol. Catal. A: Chemical 352:86–94.

Han J-K, Jia L-T, Hou B, Li D-B, Liu Y, Liu Y-C (2015) Catalytic properties of CoAl₂O₄/Al₂O₃ supported cobalt catalysts for Fischer-Tropsch synthesis, J. Fuel Chem. Technol. 43 (7): 846–851.

Ishihara H, Koga H, Kitaoka T, Wariishi H, Tomoda A, Suzuki R (2010) Structured catalyst for catalytic NO_x removal from combustion exhaust gas, Chem. Eng. Sci. 65:208–213.

Jin Q, Shen Y, Zhu S, Liu Q, Li X, Yan W (2016) Effect of praseodymium additive on CeO₂(ZrO₂)/TiO₂ for selective catalytic reduction of NO by NH₃, J. Rare Earths 34 (11): 1111–1120.

Kaplin IY, Lokteva ES, Golubina EV, Maslakov KI, Chernyak SA, Lunin VV (2017) Promoting effect of potassium and calcium additives to cerium–zirconium oxide catalysts for the complete oxidation of carbon monoxide, Kinet. Catal. 58:585–592.

Khalaji AD, Nikookar M, Fejfarova K, Dusek M (2014) Synthesis of new cobalt(III) Schiff base complex: A new precursor for preparation Co₃O₄ nanoparticles via solid-state thermal decomposition, J. Mol. Struct. 1071:6–10.

1
2
3
4 Koga H, Fukahori S, Kitaoka T, Nakamura M, Wariishi H (2008) Structured catalyst with
5
6 porous fiber-network microstructure for autothermal hydrogen production, Chem. Eng. J.
7
8 139:408–415.
9
10
11 Koga H, Fukahori S, Kitaoka T, Tomoda A, Suzuki R, Wariishi H (2006) Autothermal
12
13 reforming of methanol using paper-like Cu/ZnO catalyst composites prepared by a
14
15 papermaking technique, Appl. Catal. A: General 309:263–269.
16
17
18 Koga H, Kitaoka T, Wariishi H (2008) In situ synthesis of Cu nanocatalysts on ZnO
19
20 whiskers embedded in a microstructured paper composite for autothermal hydrogen
21
22 production, Chem. Commun. 43:5616–5618.
23
24
25 Koga H, Umemura Y, Ishihara H, Kitaoka T, Tomoda A, Suzuki R, Wariishi H (2009)
26
27 Structured fiber composites impregnated with platinum nanoparticles synthesized on a
28
29 carbon fiber matrix for catalytic reduction of nitrogen oxides, Appl. Catal. B:
30
31 Environmental 90:699–704.
32
33
34 Liotta LF, Di Carlo G, Pantaleo G, Venezia AM, Deganello G (2006) Co₃O₄/CeO₂
35
36 composite oxides for methane emissions abatement: relationship between Co₃O₄–CeO₂
37
38 interaction and catalytic activity, Appl. Catal. B: Environmental 66:217–227.
39
40
41 Liu S, Wu X, Weng D, Li M, Ran R (2015) Roles of acid sites on Pt/H-ZSM5 catalyst in
42
43 catalytic oxidation of diesel soot, ACS Catal. 5:909–919.
44
45
46 Luo JY, Meng M, Li X, Li XG, Zha YQ, Hu TD, Xie YN, Zhang J (2008) Mesoporous
47
48 Co₃O₄–CeO₂ and Pd/Co₃O₄–CeO₂ catalysts: Synthesis, characterization and mechanistic
49
50 study of their catalytic properties for low-temperature CO oxidation, J. Catal. 254:310–324.
51
52
53 Maksasithorn S, Praserttham P, Suriye K, Debecker DP (2015) Preparation of super-
54
55 microporous WO₃–SiO₂ olefin metathesis catalysts by the aerosol-assisted sol–gel process,
56
57 Microporous Mesoporous Mater. 213:125–133.
58
59
60
61
62
63
64
65

1
2
3
4 Marrero-Jerez J, Larrondo S, Rodriguez-Castellón E, Núñez P (2014) TPR, XRD and XPS
5
6 characterisation of ceria-based materials synthesized by freeze-drying precursor method,
7
8 Ceram. Int. 40:6807–6814.
9
10
11 Milt VG, Ulla MA, Miro EE (2005) NO_x trapping and soot combustion on BaCoO_{3-y}
12
13 perovskite: LRS and FTIR characterization, Appl. Catal. B: Environmental 57:13–21.
14
15
16 Mosconi S, Lick ID, Carrascull A, Ponzi MI, Ponzi EN (2007) Catalytic combustion of
17
18 diesel soot: Deactivation by SO₂ of copper and potassium nitrate catalysts supported on
19
20 alumina, Catal. Commun. 8:1755–1758.
21
22
23 Pega S, Boissiere C, Grosso D, Azais T, Chaumonnot A, Sanchez C (2009) Direct Aerosol
24
25 Synthesis of Large-Pore Amorphous Mesostructured Aluminosilicates with Superior Acid-
26
27 Catalytic Properties, Angew. Chem. Int. Ed. 48:2784–2787.
28
29
30 Piumetti M, Bensaid S, Russo N, Fino D (2016) Investigations into nanostructured ceria–
31
32 zirconia catalysts for soot combustion, Appl. Catal. B: Environmental 180:271–282.
33
34
35 Potoczna-Petru D, Kepinski L (2001) Reduction study of Co₃O₄ model catalyst by electron
36
37 microscopy, Catal. Lett. 73:41–46.
38
39
40 Quiles-Díaz S, Giménez-Mañogil J, García-García A (2015) Catalytic performance of
41
42 CuO/Ce_{0.8}Zr_{0.2}O₂ loaded onto SiC-DPF in NO_x-assisted combustion of diesel soot RSC
43
44 Adv. 5 170:18–17029.
45
46
47 Reichelt E, Heddrich MP, Jahn M, Michaelis A (2014) Fiber based structured materials for
48
49 catalytic applications, Appl. Catal. A: General 476:78–79.
50
51
52 Santos GA, Santos CMB, da Silva SW, Urquieta-González EA, Confessori PP, Sartoratto
53
54 (2012) Sol–gel synthesis of silica–cobalt composites by employing Co₃O₄ colloidal
55
56 dispersions, Colloids Surf. A Physicochem. Eng. Asp. 395:217– 224.
57
58
59
60
61
62
63
64
65

1
2
3
4 Tarka A, Zyberta M, Kindler Z, Szmurlo J, Mierzwa B, Raróg-Pilecka W (2017) Effect of
5 precipitating agent on the properties of cobalt catalysts promoted with cerium and barium
6 for NH₃ synthesis obtained by co-precipitation, Appl. Catal. A: General 532:19–25.
7
8

9
10
11 Tuler FE, Banús ED, Zanuttini MA, Miró EE, Milt VG (2014) Ceramic papers as flexible
12 structures for the development of novel diesel soot combustion catalysts, Chem. Eng. J.
13 246:287–298.
14
15

16
17
18 Tuler FE, Portela R, Ávila P, Banús ED, Miró EE, Milt VG (2015a) Structured Catalysts
19 based on sepiolite with tailored porosity to remove diesel soot, Appl. Catal. A: General
20 498:41–53.
21
22

23
24
25 Tuler FE, Gaigneaux EM, Miró EE, Milt VG, Debecker DP (2015b) Catalytic ceramic
26 papers for diesel soot oxidation: A spray method for enhanced performance, Catal.
27 Commun. 72:116–120.
28
29

30
31
32 Xu W, Cai J, Zhou J, Ou Y, Long W, You Z, Lou Y (2016) Highly Effective Direct
33 Decomposition of Nitric Oxide by Microwave Catalysis over BaMeO₃ (Me= Mn, Co, Fe)
34 Mixed Oxides at Low Temperature under Excess Oxygen, ChemCatChem 8:417–425.
35
36

37
38
39 Yang X-L, Zhang W-Q, Xia C-G, Xiong X-M, Mu X-Y, Hu B (2010) Low temperature
40 ruthenium catalyst for ammonia synthesis supported on BaCeO₃ nanocrystals, Catal.
41 Commun. 11:867–870.
42
43

44
45
46 Zhang H, Li S, Lin Q, Feng X, Chen Y, Wang J, Study on hydrothermal deactivation of
47 Pt/MnO_x-CeO₂ for NO_x-assisted soot oxidation: redox property, surface nitrates, and
48 oxygen vacancies, Environ. Sci. Pollut. Res. (2018) in press.
49
50

51
52
53
54
55 <https://doi.org/10.1007/s11356-018-1582-5>
56
57
58
59
60
61
62
63
64
65

Figure legends

Fig 1. SEM micrographs of catalytic ceramic paper prepared either using the drip impregnation procedure (a, c and e) or the spray method (b, d and f).

Fig 2. Distribution of catalytic components throughout ceramic paper prepared by drip impregnation or by the spray technique (EDS mapping).

Fig 3. (a) Infrared spectra of catalytic systems (○ Co_3O_4 and ● peroxide and superoxide species) and (b) TPR profiles.

Fig 4. XRD diffraction patterns of catalytic ceramic. Symbols: I BaCO_3 and x CeO_2 .

Fig 5. TPO stability runs of catalytic ceramic paper containing (a) Co-Ce and (b) Co-Ba-K.

Fig 6. Variation of the temperature of maximum combustion rate during successive TPO runs (values extracted from Fig. 5).

Fig 7. SEM micrographs of samples after stability runs (* samples): Co-Ce-I*, Co-Ce-S*, Co-Ba-K-I*, Co-Ba-K-S*.

Fig 8. Characterization of catalytic systems after stability runs (* samples). (a) Infrared spectra (FTIR), ○ Co_3O_4 and ● peroxide and superoxide species and (b) TPR profiles.

Fig 1S. Distribution of components throughout ceramic paper prepared either by drip impregnation or by the spray technique after stability runs (EDS mapping).

Fig 2S. Convolution of TPR profiles from the corresponding reduction peaks of Co-Ce catalytic ceramic paper.

Fig 3S. Convolution of TPR profiles from the corresponding reduction peaks of Co-Ba-K catalytic ceramic paper.

Figure

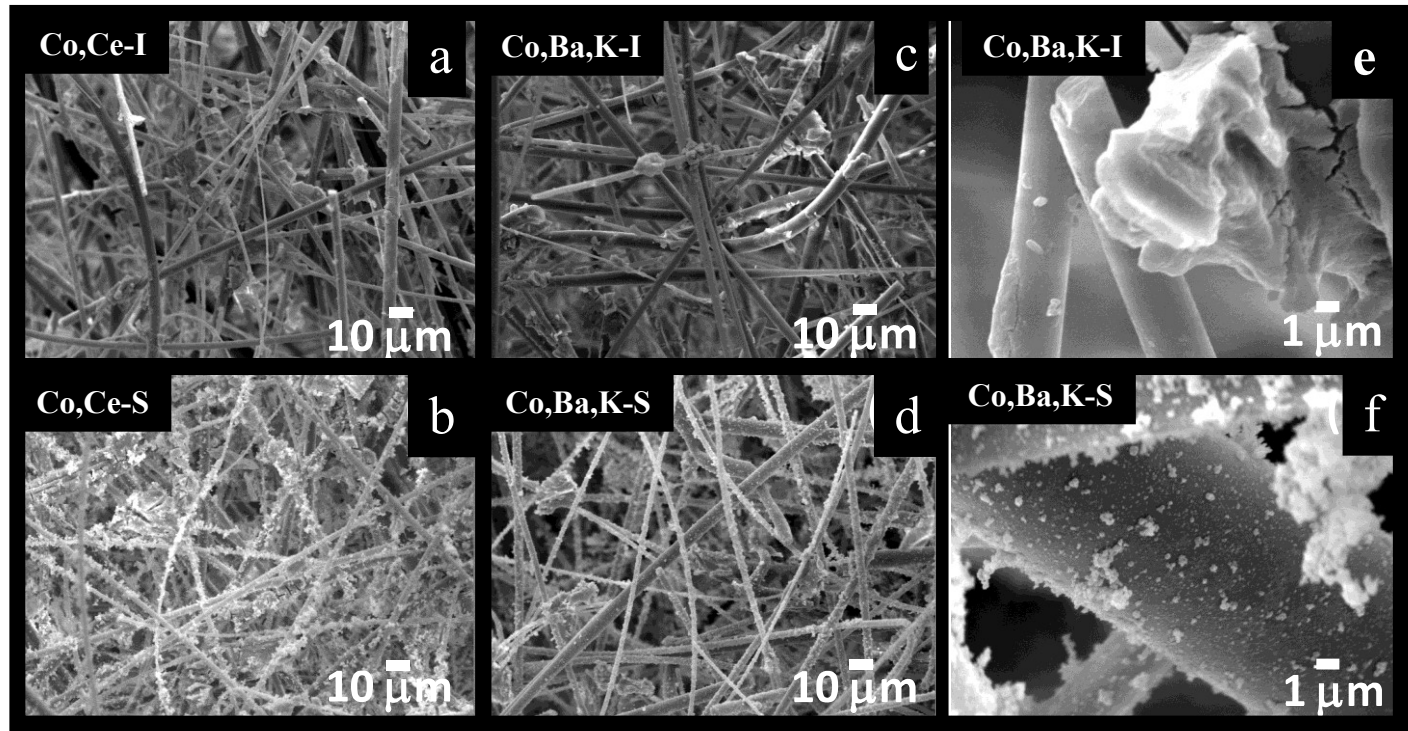


FIGURE 1

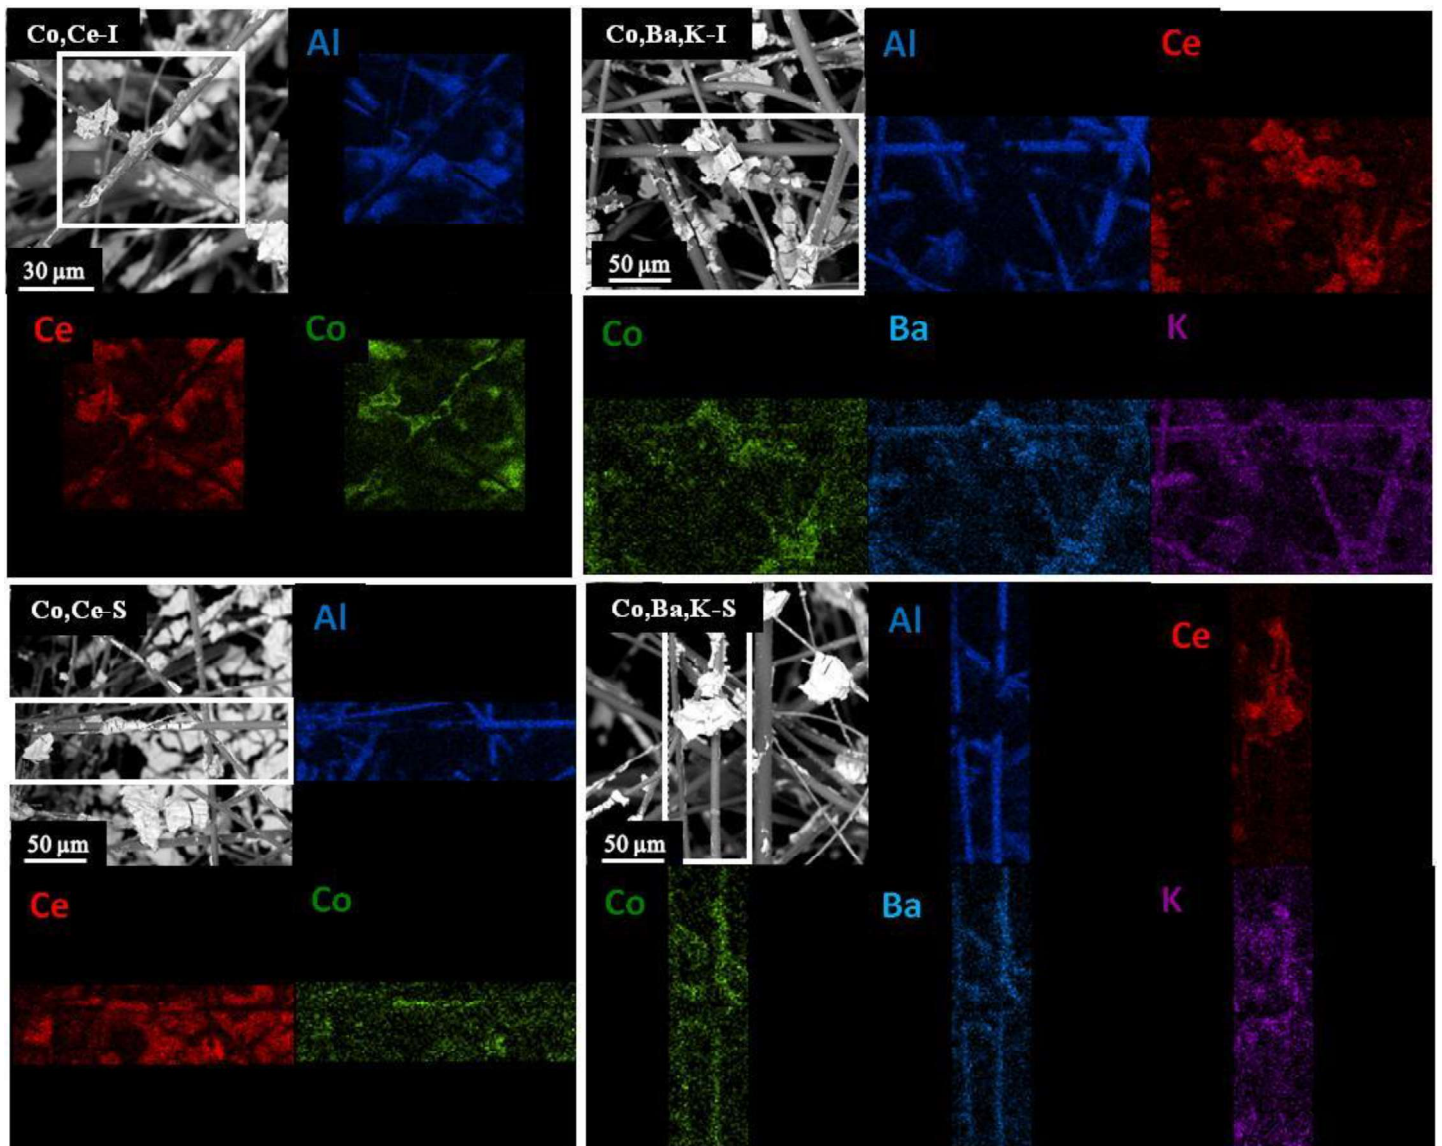


FIGURE 2

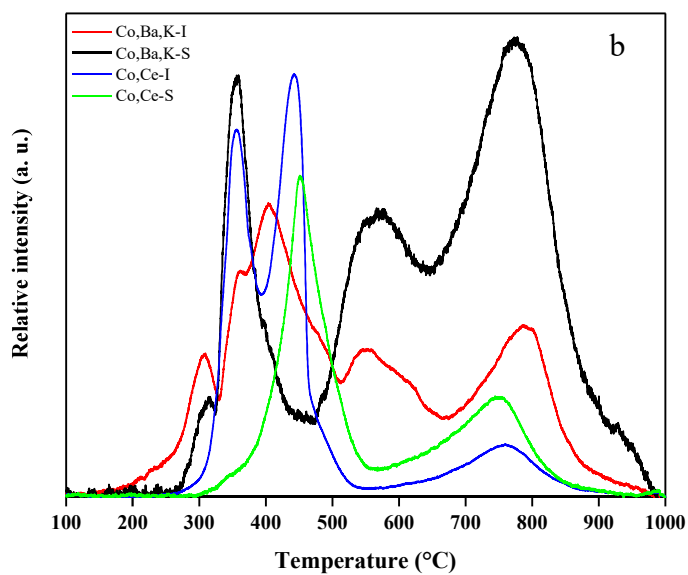
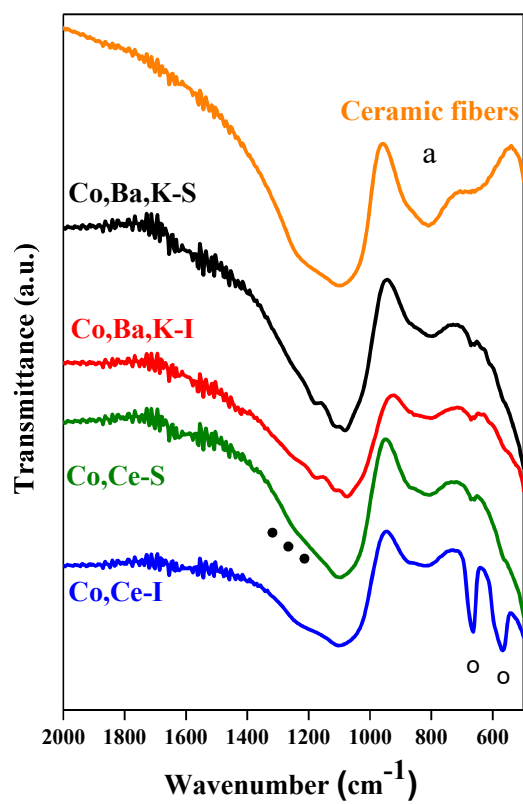


FIGURE 3

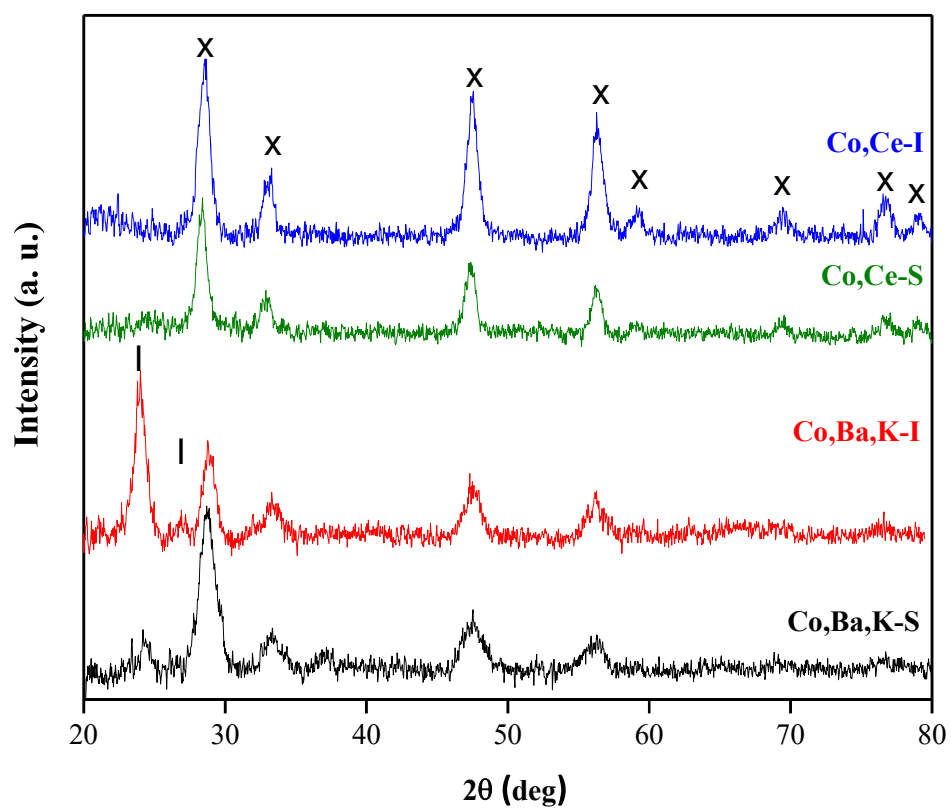


FIGURE 4

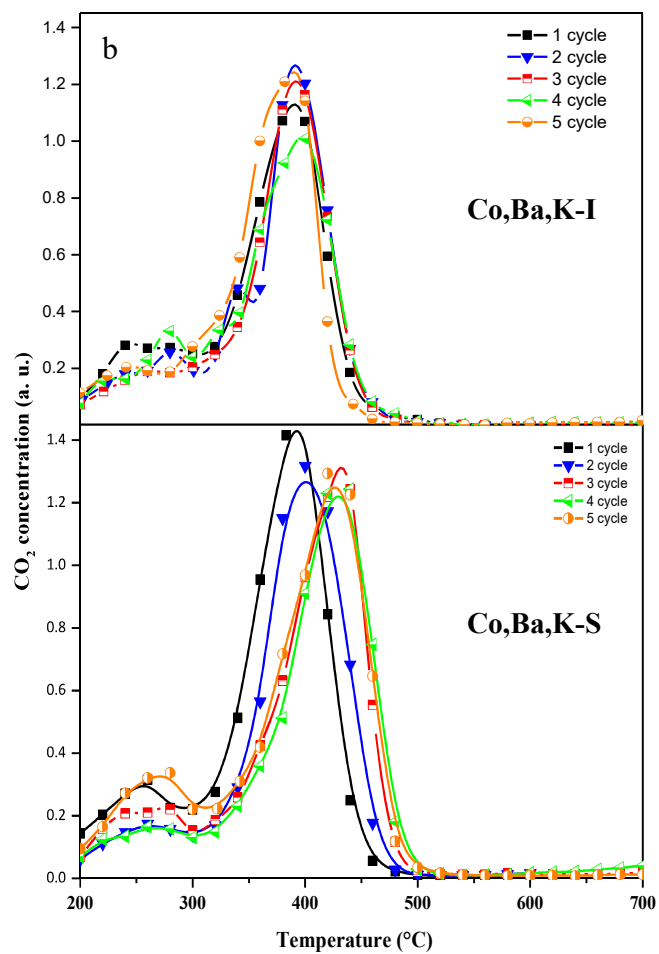
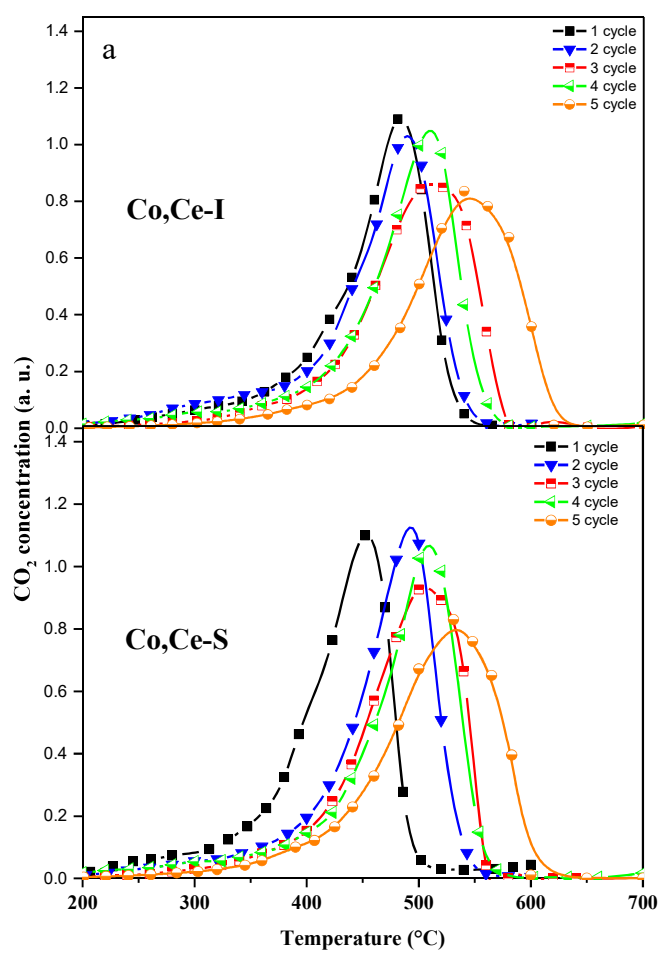


FIGURE 5

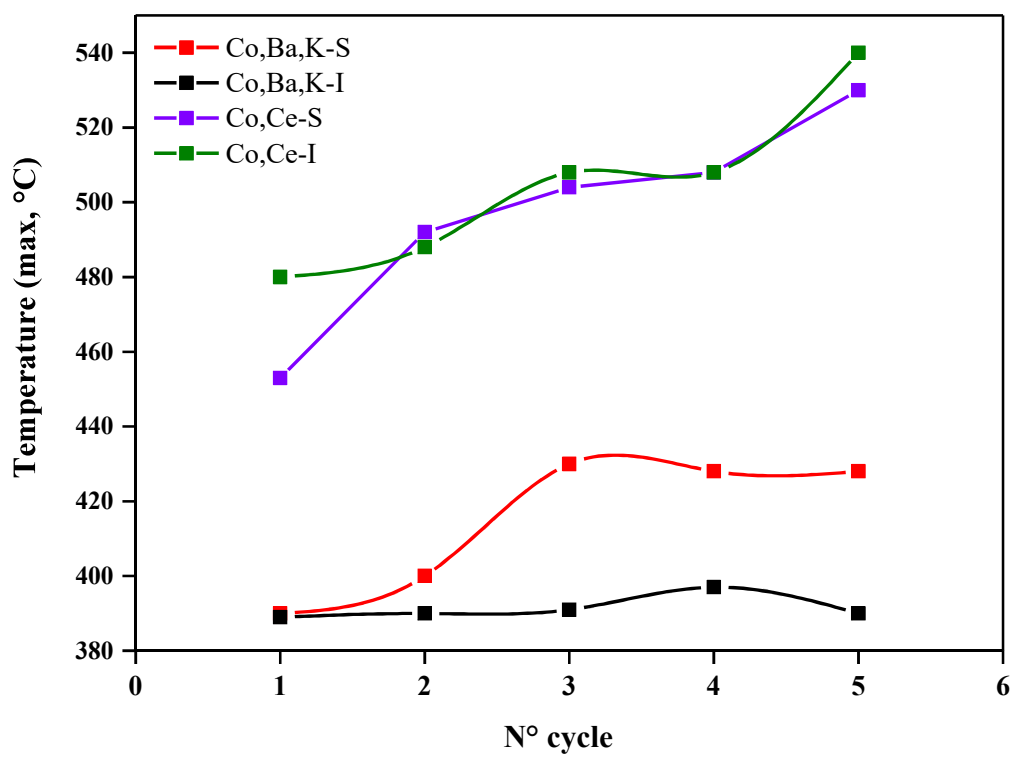


FIGURE 6

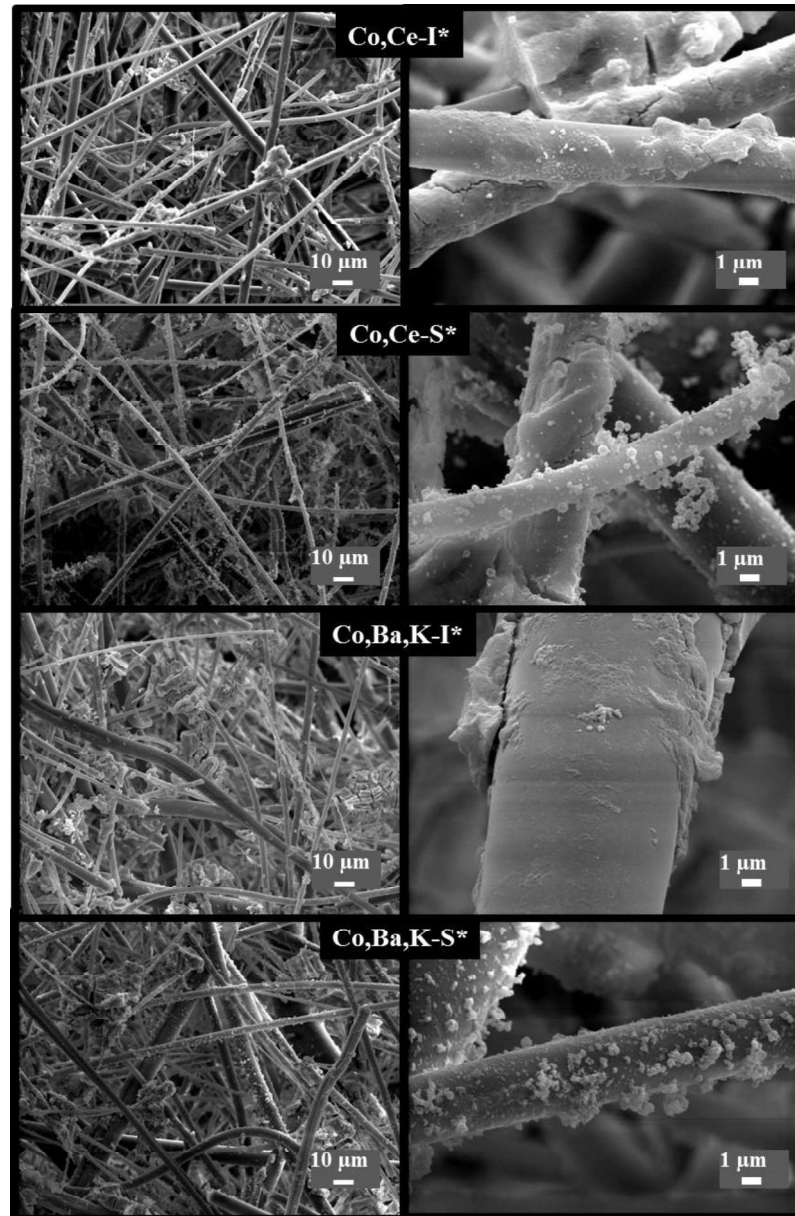


FIGURE 7

