

Hypothetical three-dimensional all- sp^2 carbon phase

G.-M. Rignanese and J.-C. Charlier

*Université catholique de Louvain,
Unité de Physico-Chimie et de Physique des Matériaux (PCPM),
European Theoretical Spectroscopy Facility (ETSF),
Place Croix du Sud 1, 1348 Louvain-la Neuve, Belgium
(Dated: August 22, 2008)*

The structural and the electronic properties of a hypothetical three-dimensional (3D) all- sp^2 carbon phase, called K_4 , are investigated using first-principles calculations. The cohesive energy per atom for this structure is found to be 1.3 eV lower than for graphite and diamond, but also more than 0.3 eV lower than for the previously proposed H-6, bct-4, and C-20 phases, also 3D all- sp^2 carbon forms. The calculated bulk modulus for the K_4 crystal is slightly higher than for the C-20 structure but lower than for the H-6 and bct-4 solids. Our analysis reveals that the relatively low cohesive energy and bulk modulus of the K_4 phase are due to the disruption of the π bonding states. The calculated density of states and band structure show that the K_4 phase is metallic.

PACS numbers: 61.50.Ah, 62.20.de, 64.60.My, 71.15.Mb, 71.15.Nc

Unquestionably, carbon is the most versatile element of the periodic table. The organics, the largest group of compounds, owe their existence to its ability to simultaneously bond to itself and a variety of heteroatoms. Moreover, pure carbon allotropes offer a unique richness and diversity : from the recently synthesized single-sheet of graphene [1], to the fullerenes [2] or the nanotubes [3].

In the quest of new hard or low compressibility materials, pure carbon allotropes have also attracted considerable attention based on the belief that the bond length and strength are related (the shorter the bonds, the stronger). Indeed, in the well-known pure carbon allotropes, the bond length strongly depends on the hybridization : from $\sim 1.42\text{\AA}$ for graphite (sp^2) to $\sim 1.54\text{\AA}$ for diamond (sp^3). However, despite its shorter bond length graphite is known as an excellent lubricant, and diamond, in contrast, is known as the hardest material. The problem is that graphite is intrinsically soft because of its two-dimensional (2D) nature. Hence, several hypothetical three-dimensional (3D) all- sp^2 networks have been proposed in the literature [4] such as H-6 [5], bct-4 [6], C-20 [7] structures (see Fig. 1), all of them revealing high bulk moduli but unfortunately smaller than the value for diamond.

Recently, T. Sunada [8] has proposed to use the structural principles of the diamond lattice to create a related crystal, called K_4 , with equal mathematical symmetry, inducing isotropic properties. In this topology, the atoms are not tetragonally but trigonally-bonded, thus constituting a hypothetical 3D all- sp^2 network (see Fig. 1). Since “*Nature favors symmetry*”, one is tempted to ask if this high-symmetry mathematical object can exist in nature as a real crystal, or if it may be synthesized with a highly versatile atomic element like carbon.

In this paper, this hypothetical 3D all- sp^2 K_4 carbon allotropic form is investigated using first-principles calculations. Its structural and electronic properties are determined and compared to those of all the other carbon

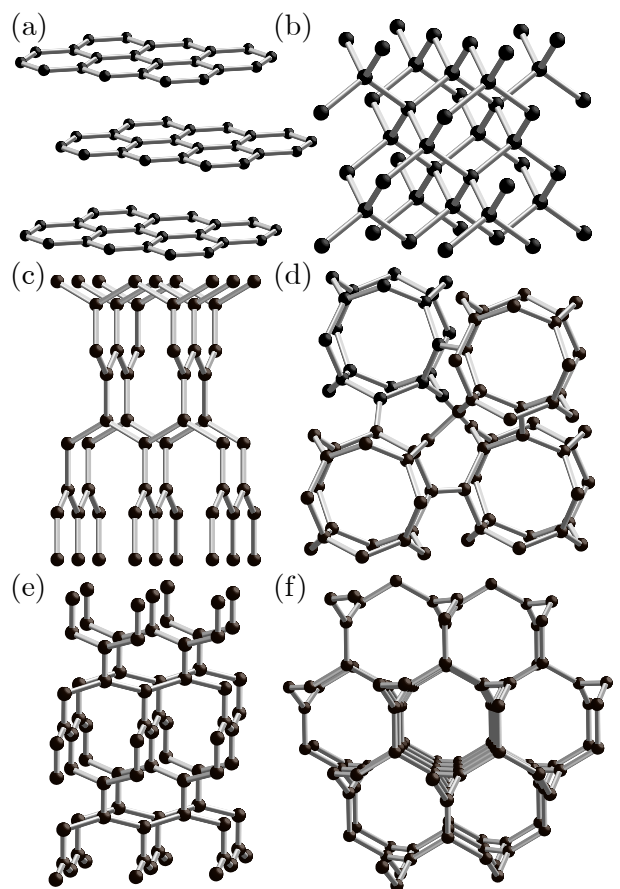


FIG. 1: Ball and stick models of the two natural carbon forms : (a) graphite and (b) diamond compared to four hypothetical 3D all- sp^2 carbon phases : (c) H-6, (d) C-20, (e) bct-4, and (f) K_4 crystals.

phases illustrated in Fig. 1. The cohesive energy per atom for the K_4 structure is more than 0.3 eV lower than for all the 3D all- sp^2 carbon forms proposed previously (H-6,

bct-4, and C-20). The bulk modulus for the K_4 crystal is slightly higher than for the C-20 structure but lower than for the H-6 and bct-4 solids. The relatively low cohesive energy and bulk modulus of this phase are discussed in terms of the disruption of the π bonding states. The K_4 phase is also found to be metallic. Our findings question the possibility to create carbon materials harder than diamond using 3D structure out of a sp^2 -bonded atomic configuration.

Throughout this study, the structural and electronic properties of the different allotropic carbon phases are investigated within a pseudo-potential [9] plane-waves approach to density functional theory (DFT), as implemented in the ABINIT code [10]. We adopt the local density approximation (LDA) and a 30 Ha cutoff to expand the electronic eigenstates. Special care is taken to sample the Brillouin zone of metallic carbon phases using various sets of irreducible k points [11]. The energy levels are populated using a Gaussian broadening [12] of 150 meV. The structural parameters are relaxed using a Broyden scheme for the forces and stresses, to values lower than 10^{-6} Ha/Bohr and 10^{-6} Ha/Bohr³, respectively.

The hypothetical K_4 structure is body-centered cubic (space group $I4_122$), with 8 atoms located at the 8a ($1/8, 1/8, 1/8$) Wyckoff positions in the conventional unit cell (the primitive unit cell only contains 4 atoms). Different views of the structure are presented in Fig. 2. This crystal has been created by similarity to that of diamond using mathematical considerations [8]. Both have a very high symmetry which results in a unique type of bond (sp^2 for the K_4 structure and sp^3 for diamond). But, while the 3D diamond lattice presents hexagonal rings in projection, the K_4 space-filling structure shows decagonal rings in projection, colored in red in Fig. 2. In addition, a significant difference between the K_4 structure and the diamond crystal is the presence of *chirality*. Namely, its mirror image cannot be superposed on the original one by a rigid motion, like for DNA, chemical enantiomers, $(n, m \neq n \neq 0)$ nanotubes, ... The *chirality* of the K_4 can be seen from the spiraling squares-octagons and triangles-nonagons, high-lighted in blue in Fig. 2 (a) and (b) respectively.

The structural properties of all the carbon phases illustrated in Fig. 1 (namely graphite, diamond, bct-4, H-6, C-20, and K_4) are summarized in Table I. For each form, we calculate the total energy over a wide range of volumes. At a given volume, the atomic positions and the unit cell are fully relaxed. We fit the resulting energies to a Birch equation of state to calculate the bulk moduli. The cohesive energy is determined by subtracting the total energy of an isolated carbon atom.

In contrast with the other 3D all- sp^2 crystals, there is only one C-C bond length in the K_4 structure (due to its high symmetry). It is calculated to be very close to that found in most sp^2 systems both in 2D, graphite (1.42Å)

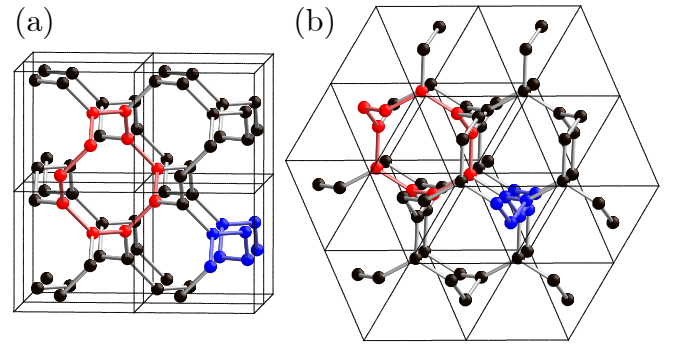


FIG. 2: [Color online] K_4 structure viewed from the (a) $[1\ 0\ 0]$ and (b) $[1\ 1\ 1]$ directions. The 8-atoms unit cell is repeated twice in each direction. The chiral property of the crystal is illustrated by high-lighting (a) the spiraling squares (blue) connected to octagons and (b) the spiraling triangles (blue) connected to nonagons. In both cases, the decagonal rings (see text) are represented in red.

or C_{60} (1.40Å, 1.45Å), and in 3D all- sp^2 crystals, H-6 and bct-4. In the C-20 structure, however, a shorter bond length (1.34Å) also appears (in agreement with Ref.[7]), which is associated to a double bond. Such an alternation of single (longer) and double (shorter) bonds is quite frequent in carbon systems (e.g. the C_{60} molecule). However, it is excluded by symmetry in the K_4 crystal.

Calculations based on the local-density approximation tend to overestimate the cohesive energy of solids but the relative energies of different atomic structures are usually reliable. The cohesive energy of the K_4 solid is found to be 8.9 eV per atom (Table I), which is ~ 1.3 eV lower than the binding energy of graphite and also ~ 0.9 eV lower than the one of C_{60} [13] within this technique. Such a low stability of the K_4 crystal compared to the other all- sp^2 forms will be explained in the following sections using a topological model based on the disruption of the π bonding.

Concerning the bulk modulus, the compressibility of the K_4 solid is predicted to be higher compared to diamond and to two other 3D all- sp^2 carbon solids (H-6, bct-4), but slightly lower than the C-20 solid phase. In Table I, a correlation can be observed between the bulk modulus and the inverse of the volume per atom (rather than the inverse of the C-C bond length as usually thought). In fact, the large volume per atom predicted for the K_4 structure is certainly responsible for such a surprisingly compressible carbon structure, as also observed for most cage-like materials like the C-20 solid [7], carbon clathrates [14] and carbon foams [15, 16].

The electronic band structure of the K_4 solid and the corresponding density of states are reported in Fig. 3, showing a metallic behavior. These can be interpreted using the procedure of Ref. [17] to generate maximally-localized Wannier functions. Usually, in all- sp^2 configurations, one $2s$ and two $2p$ atomic orbitals of each carbon

TABLE I: Equilibrium structural parameters (space group, atomic positions, volume V , lattice parameters a and c , bond lengths d_{C-C}), cohesive energy E_{coh} , and bulk modulus B calculated for the K_4 carbon solid and for H-6, bct-4, C-20, graphite and diamond. For the anisotropic structures (H-6, bct-4, and graphite), the isotropic value of the bulk modulus is also indicated between parentheses.

	K_4	H-6	bct-4	C-20	Graphite	Diamond
Space group	$I4_132$	$P6_222$	$I4_1/amd$	$Fm\bar{3}m$	$P6_3/mmc$	$Fd\bar{3}m$
Atomic positions	8a $(\frac{1}{8}, \frac{1}{8}, \frac{1}{8})$	6e (x, x, x) $x = 0.1090$	8e $(0, 0, z)$ $z = 0.0860$	32f ; 48h $(x, x, x) ; (0, y, y)$ $x = 0.1391 ; y = 0.1976$	2b ; 2c $(0, 0, \frac{1}{4}) ; (\frac{1}{3}, \frac{2}{3}, \frac{1}{4})$	8a $(\frac{1}{8}, \frac{1}{8}, \frac{1}{8})$
V ($\text{\AA}^3/\text{atom}$)	8.39	6.15	6.67	9.13	8.45	5.44
a ($\text{\AA}$)	4.063	2.604	2.500	9.007	2.434	3.518
c ($\text{\AA}$)		6.283	8.531		6.596	
d_{C-C} ($\text{\AA}$)	1.437	1.434, 1.460	1.416, 1.467	1.336, 1.457	1.405	1.523
E_{coh} (eV)	8.903	9.373	9.682	9.247	10.206	10.203
B (GPa)	273	384 (399)	354 (369)	247	29 (293)	466

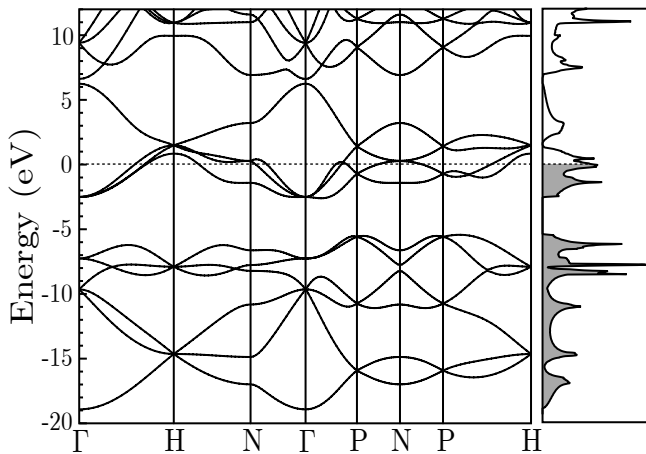


FIG. 3: Electronic band structure (left) along different high symmetry lines and the corresponding density of states (right) for the K_4 solid. The Fermi energy is positioned at zero.

atom undergo hybridization to form three sp^2 orbitals that have a trigonal planar geometry. These hybridized orbitals overlap with those of the three neighboring carbon atoms to form three σ (bonding) and three σ^* (anti-bonding) orbitals (per pair of carbon atoms). In the K_4 structure, we find six such σ orbitals, as illustrated in Fig. 4(a), for the manifold ranging from -20 to -5 eV. Higher in energy, the states localized between -3 eV and 6 eV correspond to the four (one per carbon atom) remaining $2p_z$ orbitals (where z is the direction perpendicular to the plane formed by the atom and its first-neighbors), as represented in Fig. 4(b). This separation between the lower energy σ states and the higher energy $2p_z$ states of carbon is also present in other all- sp^2 carbon materials such as graphene [18] and graphite [19].

The $2p_z$ orbital of each carbon atom overlaps with those of its first neighbors to create the delocalized π

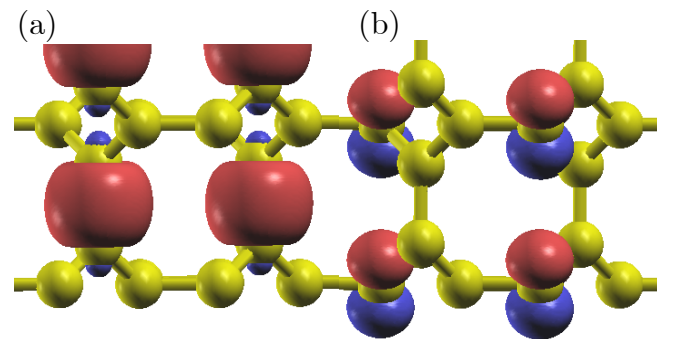


FIG. 4: [Color online] Isosurface of (a) a σ and (b) a $2p_z$ Wannier function in the K_4 crystalline structure (yellow). The positive and negative lobes of the localized atomic orbitals, are illustrated in blue and red, respectively.

(bonding) and π^* (anti-bonding) orbitals. However, the amount of overlap depends on the angle between the $2p_z$ orbitals of the neighboring carbon atoms (also called misalignment angle ϕ in Haddon's theory [20, 21]). When the angle increases, the π bonding between these atoms, and thus the binding energy of the solid decreases. In graphene, all the $2p_z$ orbitals are aligned with the direction perpendicular to the sheet [22], leading to a strong π bonding interaction between carbon neighbors, and thus contributing to the high stability of the system. In contrast, in the K_4 solid, the $2p_z$ orbitals between neighboring atoms are all strongly misaligned, leading to a disruption of the π bonding network and to a metastability of this phase. This effect of disrupting the π bonding state has already been observed in fullerenes [23] and in the three other 3D all- sp^2 solids [5–7].

In fact, the local environment of each atom influences its ability of to form these π bonds with its neighbors, and hence the stability of the crystal. The differences in

cohesive energy for 3D all- sp^2 solids reflect the amount of misaligned $2p_z$ orbitals in the structure. Graphite has all its $2p_z$ orbitals perfectly aligned and is the most stable crystal. Conversely, all the $2p_z$ orbitals are all misaligned in the K_4 solid which is the most unstable. The C-20 structure, which presents only 1/5 of its bonds with well-aligned $2p_z$ orbitals, is less stable than the H-6 and bct-4 ones, which both have 2/3 of their bonds with well-aligned $2p_z$ orbitals. These two solids only differ by the value of the misalignment angles ($\phi=60^\circ$ in H-6 and $\phi=90^\circ$ in bct-4), it is thus more dubious to compare their stability using such a qualitative model.

In order to further investigate these topological considerations, other 3D all- sp^2 structures containing more bonds with well-aligned $2p_z$ orbitals were generated based on the H-6 and bct-4 solids, since for symmetry reasons this could not be done based on the K_4 crystal. As shown in Fig. 5(a), the H-6 structure can be seen as consisting of three families of limited-dimension graphene planes (colored in red, green, and blue) with well-aligned $2p_z$ orbitals, connected by bonds (in violet, yellow, and turquoise) with misaligned $2p_z$ orbitals with $\phi=60^\circ$ (it is actually the angle from one plane to another). As reported in Fig. 5(b), the bct-4 crystal only has two such families of planes (in red and blue) and the connecting bonds (in pink and violet) present a misalignment of 90° . For both systems, the number of bonds with well-aligned $2p_z$ orbitals can easily be increased by extending the dimension of the families of graphene planes to form hypergraphite as suggested in Refs. [24–26]. This is illustrated at the bottom of Fig. 5. The amount of such bonds goes from 2/3 to 5/6 when going from the H-6 and bct-4 crystals to their corresponding extended structures. The cohesive energy of the extended systems are found to be increased by $\simeq 0.1\text{eV/atom}$ with respect to the original ones, confirming the trend already observed for the other all- sp^2 solids.

In contrast, the bulk moduli of the extended structures 384 and 350 GPa are basically the same as for the H-6 and bct-4 crystals, respectively. This indicates that increasing the number of bonds with well-aligned $2p_z$ orbitals is probably not the route to follow to obtain a 3D all- sp^2 material harder than diamond. On the other hand, not only the bulk moduli but also the volume per atom are not changed in the extended structures. This further confirms our observation that the bulk modulus correlates with the inverse of the volume per atom. This suggests that trying to reduce the volume per atom might be a more appropriate solution. But this is not possible for 3D all- sp^2 materials. Thus, it seems unavoidable to us that such systems will present a bulk modulus lower than diamond.

In conclusion, a hypothetical 3D all- sp^2 crystal, named K_4 , having a remarkable symmetric and isotropic structure mathematically similar to that of diamond, has been investigated using first-principles approach. The equilib-

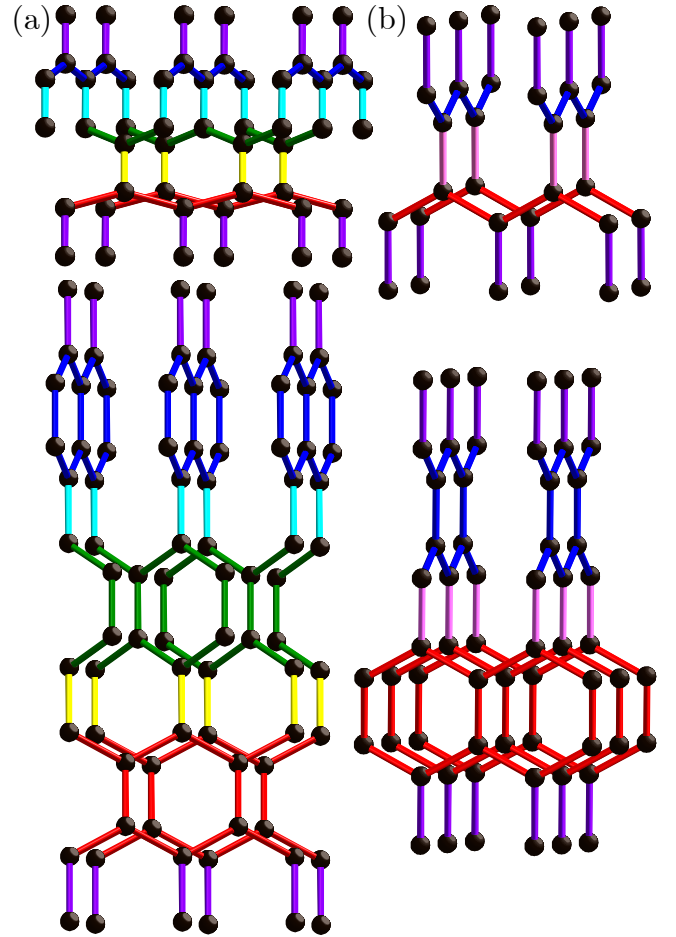


FIG. 5: [Color online] Ball and stick models of the (a) H-6 and (b) bct-4 crystals (top) and their corresponding extended structures (bottom). The bonds with well-aligned $2p_z$ orbitals are colored in pink, violet, turquoise, and yellow.

rium geometry (internal and lattice parameters), the cohesive energy, and the bulk moduli were calculated and compared to those of other 3D all- sp^2 crystals. The carbon-carbon bond length is close to graphite and to other 3D all- sp^2 systems such as H-6 and bct-4. Due to the symmetry of the K_4 solid, all the bonds are equivalent so that alternation of single and double bonds like in the C-20 crystal is not possible. The cohesive energy per atom for the K_4 structure is quite low: it is significantly lower than that of all the 3D all- sp^2 carbon forms proposed previously (H-6, bct-4, and C-20). This low cohesive energy has been explained by the misalignment of the $2p_z$ orbitals in all the bonds. The bulk modulus for the K_4 crystal is found to be lower than for the H-6 and bct-4 solids, but slightly higher than for the C-20 structure. The electronic properties (band structure and density of states) have also been calculated. The K_4 phase is found to be metallic, with the partially occupied manifold close to the Fermi energy corresponding to the four $2p_z$ orbitals.

Even though the K_4 structure is found to be metastable for carbon, it is an interesting example of a 3D all- sp^2 network. Its X-ray signature should be easily identifiable experimentally with respect to the other carbon structures, as shown in Fig. 6. If the K_4 solid was to be synthesized, it certainly would have interesting material properties. For instance, assuming an electron-phonon coupling analogous to graphite ($\pm$ same C-C bond length) and its intrinsic metallic behavior, the K_4 solid might be an interesting superconducting material.

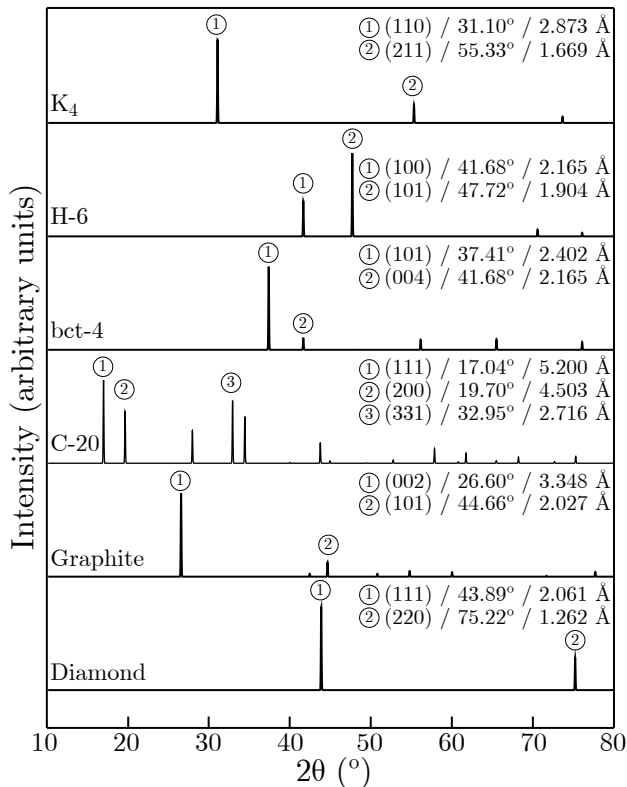


FIG. 6: X-Ray diffraction patterns simulated [27] for the different carbon structures considered in the present study. The Miller indices, the precise value of 2θ , and the corresponding interplane distance are reported for the most prominent peaks of each structure.

G.M.R. and J.C.C. acknowledge the FNRS of Belgium for financial support. Parts of this work are directly connected to the Belgian Program on Interuniversity Attraction Poles (PAI6) on “Quantum Effects in Clusters and Nanowires”, to the ARC sponsored by the Communauté Française de Belgique and to the NANOQUANTA European Network of Excellence. Computational resources have been provided by the Université catholique de Lou-

vain : all the numerical simulations have been performed on the LEMAITRE computer of the CISM.

- [1] K.S. Novoselov, A.K. Geim, S.V. Morozov, D. Jiang, S.V. Dubonos, I.V. Girgorieva, and A.A. Firsov, *Science* **306**, 666-669 (2004).
- [2] H.W. Kroto, J.R. Heath, S.C. O’Brien, R.F. Curl and R.E. Smalley, *Nature*, **318**, 162-163 (1985).
- [3] S. Iijima, *Nature* **354**, 56-58 (1991).
- [4] R. Hoffman, T. Hughbanks, M. Kertesz, and P.H. Bird, *J. Am. Chem. Soc.* **105**, 4831-4832 (1983).
- [5] A.Y. Liu, M.L. Cohen, K.C. Hass, and M.A. Tamor, *Phys. Rev. B* **43**, 6742-6745 (1991).
- [6] A.Y. Liu and M.L. Cohen, *Phys. Rev. B* **45**, 4579-4581 (1992).
- [7] M. Côté, J.C. Grossman, M.L. Cohen, and S.G. Louie, *Phys. Rev. B* **58**, 664-668 (1998).
- [8] T. Sunada, *Not. Am. Math. Soc.* **55**, 208-215 (2008).
- [9] N. Troullier and J.L. Martins, *Phys. Rev. B* **43**, 1993-2006 (1991).
- [10] X. Gonze *et al.*, *Comput. Mater. Sci.* **25**, 478-492 (2002).
- [11] H.J. Monkhorst and J.D. Pack, *Phys. Rev. B* **13**, 5188-5192 (1976).
- [12] M. Methfessel and A.T. Paxton, *Phys. Rev. B* **40**, 3616-3621 (1989).
- [13] X. Rocquefelte, G.-M. Rignanese, V. Meunier, H. Terrones, M. Terrones, and J.-C. Charlier, *Nano Lett.* **4**, 805-810 (2004).
- [14] X. Blase, P. Gillet, A. San Miguel, and P. Mélinon, *Phys. Rev. Lett.* **92**, 215505 (2004).
- [15] K. Umamoto, S. Saito, S. Berber, and D. Tománek, *Phys. Rev. B* **64**, 193409 (2001).
- [16] A. Kuc and G. Seifert *Phys. Rev. B* **74**, 214104 (2006).
- [17] N. Marzari and D. Vanderbilt, *Phys. Rev. B* **56**, 12847-12865 (1997).
- [18] J.-C. Charlier, P.C. Eklund, J. Zhu and A.C. Ferrari, in *Carbon Nanotubes* (Eds. A. Jorio, G. Dresselhaus, M. S. Dresselhaus, Springer-Verlag Berlin Heidelberg 2008) *Topics Appl. Physics* **111**, 673709 (2008).
- [19] J.-C. Charlier, X. Gonze, and J.-P. Michenaud, *Phys. Rev. B* **43**, 4579-4589 (1991).
- [20] R.C. Haddon, *Chem. Phys. Lett.* **125**, 231 (1986).
- [21] R.C. Haddon, *J. Am. Chem. Soc.* **108**, 2837 (1986).
- [22] P.R. Wallace, *Phys. Rev.* **71**, 622 (1947).
- [23] J.C. Grossman, M. Côté, S.G. Louie, and M.L. Cohen, *Chem. Phys. Lett.* **284**, 344-349 (1998).
- [24] Y. Takagi *et al.*, *Synth. Met.* **103**, 2574 (1999).
- [25] Y. Takagi, M. Fujita, and K. Kusakabe, *Mol. Cryst. and Liq. Cryst.* **340**, 379 (2000).
- [26] Y. Takagi *et al.*, <http://xxx.yukawa.kyoto-u.ac.jp/abs/cond-mat/0001027>
- [27] D.C. Palmer, computer program CrystalDiffra 5.1.6 (CrystalMaker Software, Bicester, Oxfordshire, England, 2008).