

RESEARCH ARTICLE

WILEY

Stochastic multiscale modeling of crack propagation in random heterogeneous media

Darith-Anthony Hun¹ | Johann Guilleminot²  | Julien Yvonnet¹  | Michel Bornert³

¹Laboratoire Modélisation et Simulation Multi Échelle MSME UMR 8208 CNRS, Université Paris-Est, Marne-la-Vallée, France

²Department of Civil and Environmental Engineering, Duke University, Durham, North Carolina

³Laboratoire Navier, CNRS UMR8205, ENPC, IFSTTAR, Université Paris-Est, Marne-la-Vallée, France

Correspondence

Johann Guilleminot, Department of Civil and Environmental Engineering, Duke University, Durham, NC 27708.

Email: johann.guilleminot@duke.edu

Summary

A stochastic approach to model crack propagation in random heterogeneous media, using mesoscopic representations of elastic and fracture properties, is presented. In order to obtain reference results, Monte-Carlo simulations are first conducted on microstructural samples in which a pre-existing crack is propagated by means of a phase-field approach. These computations are used to estimate the subscale-induced randomness on the macroscopic response of the domain. Mesoscopic descriptors are then introduced to investigate scale transition. Elasticity tensor random fields are specifically defined, at that stage, through a moving-window upscaling approach. The mesoscopic fracture toughness, which is assumed homogeneous and deterministic, is identified by solving an inverse problem involving the macroscopic peak force. A stochastic model is subsequently constructed in which the mesoscopic elasticity is described as a non-Gaussian random field. This model allows the multiscale-informed elastic counterpart in the phase-field formulation to be sampled without resorting to computational homogenization. The results obtained with the sample-based and model-based mesoscopic descriptions are finally compared with those corresponding to the full-scale microscopic model. It is shown, in particular, that the mesoscopic elasticity-phase-field formulation associated with statically uniform boundary conditions enables the accurate predictions of the mean elastic response and mean peak force.

KEYWORDS

crack propagation, mesoscale, phase-field method, random field, stochastic analysis, uncertainty quantification

1 | INTRODUCTION

Modeling the damage and strength properties in heterogeneous brittle or quasi-brittle materials is of major interest in civil and mechanical engineering, biomechanics, and many other areas of engineering. In such complex materials like concrete, cementitious materials, cortical bone, or fiber/particle-reinforced composites, the main damage mechanisms are due to the initiation and propagation of crack networks at the microscale. However, in most applications, modeling the crack propagation at the scale of constituents up to the macroscale is, in general, not tractable. In the recent years, a few attempts have been devoted to multiscale modeling of damage from microscale crack propagation, including, among many others: FE²-approaches considering separated scales and microscale nonlinear damage,^{1,2} extended FE²

techniques with discontinuities at the macroscale,^{3–6} domain decompositions methods embedding discontinuities,^{7–9} or more recently methodologies enabling the identification of regularized damage models at the macroscale from microscale calculations.^{10,11}

In the mentioned works, only deterministic geometries and crack paths were considered. Since microstructural randomness strongly impacts the macroscopic response of (quasi-) brittle materials in various ways, ranging from size effects^{12–15} to high stochasticity in failure patterns and ultimate properties,^{16–18} the development of approaches incorporating multi-scale and probabilistic ingredients all together is a natural path to extend the predictive capabilities in fracture simulations. The main objective of this work is to propose a stochastic multiscale-informed phase-field approach to model crack propagation in heterogeneous media. In the proposed framework, the parameters involved in the elasticity-phase-field formulation are specifically defined through multiscale analysis with nonseparated scales. This particular setting ensures consistency with critical subscale information and allows for the propagation of stochasticity at the macroscopic level. Similar ideas were pursued in the very recent work,¹⁹ with a few noticeable differences though. First, the approach developed in the aforementioned reference is concerned with dynamical fracture, solved using an asynchronous spacetime discontinuous Galerkin method, and is focused on fracture strength random fields. A phase-field approach to brittle fracture modeling is alternatively considered and extended in this paper, in which validation is further assessed on a macroscopic quantity of interest. Second, while both contributions invoke information theory as a rationale to define probability measures, stochastic modeling aspects and related methodological issues are addressed more extensively hereinafter. Note also that crack paths are simulated in the sequel by propagating a pre-existing crack, whereas crack nucleation sites are identified, for each sample of the microstructure, as the weakest material points in the work of Acton et al.¹⁹

This paper is organized as follows. The computational approach enabling the description of crack propagation at the microscopic scale is first detailed in Section 2. The phase-field formulation is introduced, and reference stochastic computations are performed on a prototypical random microstructure. The description of crack propagation using mesoscopic descriptors is next addressed in Section 3. Methodologies to define and subsequently identify these descriptors are introduced and applied to the aforementioned microstructure. The relevance of the framework is finally assessed by comparing macroscopic predictions based on either the reference microscopic model or the proposed mesoscopic approach.

2 | STOCHASTIC MODELING OF CRACK PROPAGATION AT MICROSCALE

2.1 | Formulation

We consider an open bounded domain $\Omega \subset \mathbb{R}^m$, $m = 2, 3$, with boundary $\partial\Omega$, subjected to Dirichlet and Neumann boundary conditions $\mathbf{u}_D$ and $\mathbf{t}_N$ on the corresponding boundaries $\partial\Omega_u$ and $\partial\Omega_t$, respectively, with $\partial\Omega_u \cup \partial\Omega_t = \partial\Omega$ and $\partial\Omega_u \cap \partial\Omega_t = \emptyset$ (see Figure 1 (a)). The total energy of the cracked solid is given by

$$\mathcal{E}(\mathbf{u}, \Gamma) = \int_{\Omega \setminus \Gamma} \Psi(\mathbf{u}, \Gamma) d\Omega + g_c \mathcal{H}^{m-1}(\Gamma) - \int_{\partial\Omega_t} \mathbf{t}_N \cdot \mathbf{u} d\Gamma, \quad (1)$$

where $\mathbf{u}$ denotes the displacement vector, Ψ is the elastic strain density function, g_c is the fracture toughness, or critical energy release rate in the sense of Griffith, and $\mathcal{H}$ the Hausdorff measure of dimension $m - 1$ representing the discontinuous crack shape Γ . In this work, we adopt the variational approach to fracture as proposed by Francfort and Marigo²⁰ and Bourdin et al.^{21,22} and developed in an efficient computational framework in the work of Miehe et al.,²³ called in the literature the phase field approach to fracture. The aforementioned energy form can be replaced by a regularized one,^{24,25} given by the following:

$$E(\mathbf{u}, d) = \int_{\Omega} \Psi(\mathbf{u}, d) d\Omega + g_c \int_{\Omega} \gamma(d) d\Omega - \int_{\partial\Omega_t} \mathbf{t}_N \cdot \mathbf{u} d\Gamma, \quad (2)$$

where γ is a crack density function, whose model can be chosen among several possible forms, leading to a class of shapes for the regularized damage field near the crack (see, eg, the work of Borden et al.²⁶). In this regularized framework, the cracks are no more described by surfaces but by a smooth field $\mathbf{x} \mapsto d \in [0, 1]$ (see Figure 1B). For example, the so-called first-order model is associated with

$$\gamma(d) = \frac{1}{2\ell} d^2 + \frac{\ell}{2} \nabla(d) \cdot \nabla(d), \quad (3)$$

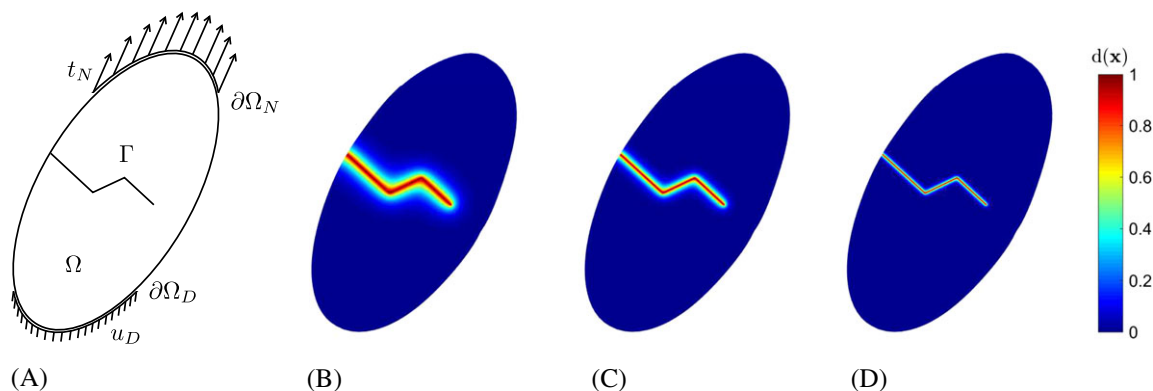


FIGURE 1 Panel (A): sharp description of a cracked solid. Panels (B), (C), and (D): smeared description within the phase field framework, showing damage profile $\mathbf{x} \mapsto d(\mathbf{x})$ for different values of the regularization length ℓ (in this figure, L denotes the characteristic length of the domain, here of the minor axis of the ellipsoidal shape). A, no phase-field regularization; B, $\ell = (1/10)L$; C, $\ell = (1/20)L$; D, $\ell = (1/50)L$

where $\ell \in \mathbb{R}^+$ is a regularization length associated to the regularized description of the cracks (see Figure 1C) such that $\ell \ll \Omega$. Discussions about the choice of ℓ can be found in, eg, related works.²⁷⁻²⁹ Owing to a slight abuse of notation, the strain energy function in Equation (2) is decomposed as follows²³:

$$\Psi([\epsilon], d) = (D(d) + \eta)\Psi^+([\epsilon]^+) + \Psi^-([\epsilon]^-), \quad (4)$$

where $d \mapsto D(d)$ denotes the (stiffness) degradation function and $0 < \eta \ll 1$ is a small regularizing parameter ensuring the well-posedness of the boundary value problem. In this work, the quadratic function $D(d) = (1 - d)^2$ is used (see, eg, the works of Miehe et al²³ and Kuhn et al³⁰). The aforementioned decomposition only involves damage in tension and avoids self-interpenetration while taking into account self-contact within the crack automatically.²³ Furthermore, Ψ^+ and Ψ^- denote parts of the strain density related to tensile and compressive parts of the strain tensor, respectively. For an isotropic medium, it leads to (see the work of Miehe et al²³) the following:

$$\Psi^\pm([\epsilon]) = \frac{\lambda}{2} \left(\langle \text{Tr}([\epsilon]) \rangle^\pm \right)^2 + \mu \text{Tr} \left\{ ([\epsilon]^\pm) \right\}, \quad (5)$$

where $\text{Tr}(\cdot)$ is the trace operator and $\mathbf{x} \mapsto \lambda(\mathbf{x})$ and $\mathbf{x} \mapsto \mu(\mathbf{x})$ are the field of Lamé's constants. In Equation (5), $[\epsilon]^+$ and $[\epsilon]^-$ are such that $[\epsilon] = [\epsilon]^+ + [\epsilon]^-$ and are defined by the spectral decomposition

$$[\epsilon]^\pm = \sum_{i=1}^m \langle \kappa_i \rangle^\pm \boldsymbol{\varphi}^{(i)} \otimes \boldsymbol{\varphi}^{(i)}, \quad (6)$$

in which $\{(\kappa_i, \boldsymbol{\varphi}^{(i)})\}_{i=1}^m$ are the pairs of associated eigenvalues and eigenvectors of the strain tensor $[\epsilon]$, and $\langle \cdot \rangle^\pm$ is the operator given by

$$\langle z \rangle^\pm = \frac{1}{2}(z \pm |z|), \quad \forall z \in \mathbb{R}. \quad (7)$$

Variation of (2) with respect to $\mathbf{u}$ and d leads to the coupled equations

$$\begin{cases} \frac{\eta}{\ell} (d - \ell^2 \Delta d) - 2(1 - d) \mathcal{H}([\epsilon]) = 0, \\ \nabla \cdot [\sigma(\mathbf{u}, d)] = \mathbf{0}, \end{cases} \quad (8)$$

where $\nabla \cdot (\cdot)$ is the divergence operator and $\mathcal{H}$ is a strain density history function, used to prescribe damage irreversibility²³

$$\mathcal{H}(\mathbf{x}, t) = \max_{\tau \in [0, t]} \{ \Psi^+(\mathbf{x}, \tau) \}. \quad (9)$$

The stress tensor for the damaged material reads, for an isotropic material, as follows:

$$[\sigma(\mathbf{u}, d)] = \frac{\partial \Psi}{\partial [\epsilon]} = (D(d) + \eta) \left\{ \lambda \langle \text{Tr}([\epsilon]) \rangle^+ [1] + 2\mu [\epsilon]^+ \right\} + \lambda \langle \text{Tr}([\epsilon]) \rangle^- [1] + 2\mu [\epsilon]^-.$$

The system of Equation (8) is complemented by the following boundary conditions:

$$\begin{cases} \mathbf{u} = \mathbf{u}_D \text{ on } \partial\Omega_u, \\ [\boldsymbol{\sigma}]\mathbf{n} = \mathbf{t}_N \text{ on } \partial\Omega_t, \\ \nabla d \cdot \mathbf{n} = 0 \text{ on } \partial\Omega, \end{cases} \quad (10)$$

where $\nabla(\cdot)$ is the gradient operator, $\mathbf{u}_D$ and $\mathbf{t}_N$ are prescribed vector fields of displacements and tractions, and $\mathbf{n}$ is the outward-pointing normal vector on $\partial\Omega$ (see Figure 1A). The classical weak form associated with Equation (8) is given by

$$\begin{cases} \int_{\Omega} \left\{ \left(2\mathcal{H} + \frac{g_c}{\ell} \right) d\delta d + g_c \ell \nabla d \cdot \nabla(\delta d) \right\} d\Omega = \int_{\Omega} 2\mathcal{H} \delta d d\Omega, \\ \int_{\Omega} [\boldsymbol{\sigma}(\mathbf{u}, d)] : [\boldsymbol{\epsilon}(\delta \mathbf{u})] d\Omega = \int_{\partial\Omega_t} \mathbf{t}_N \cdot \delta \mathbf{u} dS, \end{cases} \quad (11)$$

where $(\delta d, \delta \mathbf{u})$ are test functions belonging to appropriate functional spaces. It should be noticed that, in the phase field method, crack propagation is described through the evolution of the damage field $\mathbf{x} \mapsto d(\mathbf{x})$, which is updated at each load step by solving the coupled Equation 8 (under Equation (10)). Algorithmic details on the method can be found in, eg, the works of Miehe et al.²³ and Nguyen et al.²⁹

Note at this point that Equation (5) encapsulates the stochastic aspect of the propagation at microscale because the field $\mathbf{x} \mapsto \llbracket C(\lambda(\mathbf{x}), \mu(\mathbf{x})) \rrbracket$ corresponds to a realization of the elasticity tensor random field $\{ \llbracket C(\lambda(\mathbf{x}), \mu(\mathbf{x})) \rrbracket, \mathbf{x} \in \Omega \}$ given by

$$\llbracket C(\mathbf{x}) \rrbracket = \sum_{i=1}^{N_p} \mathbb{1}_{\Omega_i}(\mathbf{x}) \llbracket C^i(\lambda(\mathbf{x}), \mu(\mathbf{x})) \rrbracket, \quad (12)$$

where $\{ \mathbb{1}_{\Omega_i}(\mathbf{x}), \mathbf{x} \in \Omega \}$ and $\llbracket C^i(\lambda(\mathbf{x}), \mu(\mathbf{x})) \rrbracket$ are the indicator function and elasticity tensor of phase i (assumed to be isotropic here), occupying domain Ω_i , and the domain Ω is assumed to contain N_p constitutive phases. For random microstructures, the indicator functions are, indeed, non-Gaussian random fields; in practice, it is thus required to proceed to, eg, Monte Carlo simulations of these fields and to solve the coupled elasticity-phase-field problem for each realization of Ω . This strategy allows the variability in crack paths (and consequently, in the nonlinear part of the macroscopic response) to be simulated at microscale. This point is specifically illustrated in the next section.

2.2 | Computing realizations of crack paths at the microscale

In this section, we describe the Monte Carlo approach used to generate realizations of crack paths at the microscale. These realizations will be used, in Section 3.3, to identify a mesoscale stochastic model constructed in Section 3.2.1. In order to illustrate the methodology throughout this paper, a prototypical stationary isotropic random microstructure made up of a homogeneous matrix and monodisperse spheres is selected hereinafter ($N_p = 2$). A 2D square domain $\Omega = [0, L]^2$ is considered (that is, $m = 2$), with $L = 1$ mm, and the radius of the inclusions is set to $R = 0.04 \times L$. Plane strain conditions are assumed. A set of $\theta^{obs} = 1000$ realizations was generated by using the molecular-dynamics-type algorithm proposed in the work of Zamponi³¹ for hard-sphere packings (under periodic boundary conditions (PBCs)).

Each sample is periodized and contains $N_{inc} = 50$ nonoverlapping heterogeneities. Independent realizations of this microstructure are shown in Figure 2.

The constitutive materials are assumed isotropic, and the bulk and shear moduli are denoted as (k_m, μ_m) and (k_i, μ_i) for the matrix and inclusions, respectively. Accordingly, $g_{c,m}$ and $g_{c,i}$ denote the toughnesses of the matrix and inclusions. These properties are chosen such that the mechanical contrast α satisfies $\alpha = k_i/k_m = \mu_i/\mu_m = g_{c,i}/g_{c,m}$, where the

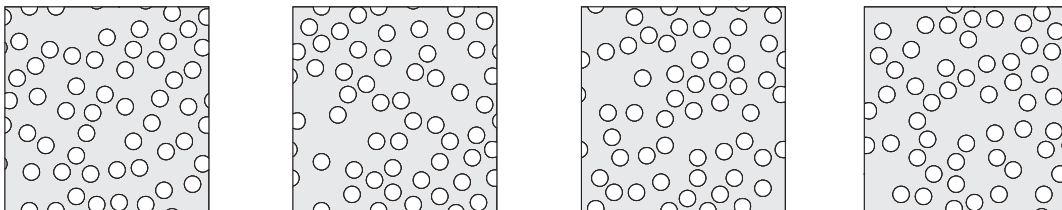


FIGURE 2 Four independent realizations of the periodized random microstructure

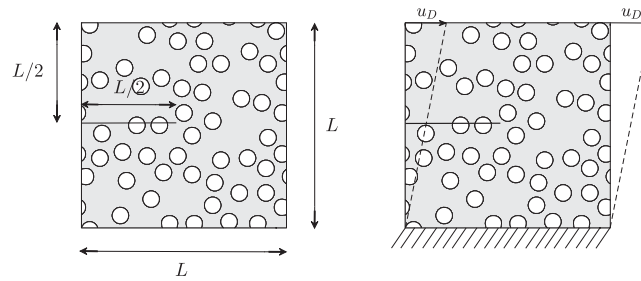


FIGURE 3 Boundary conditions applied to the domain and initial crack

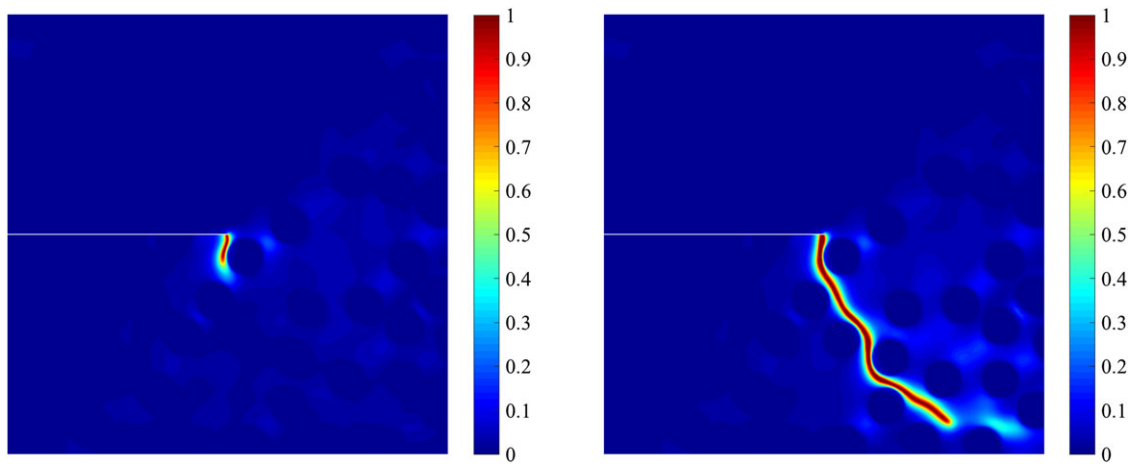


FIGURE 4 Evolution of the damage field $\mathbf{x} \mapsto d(\mathbf{x})$ for the microstructure shown in Figure 3

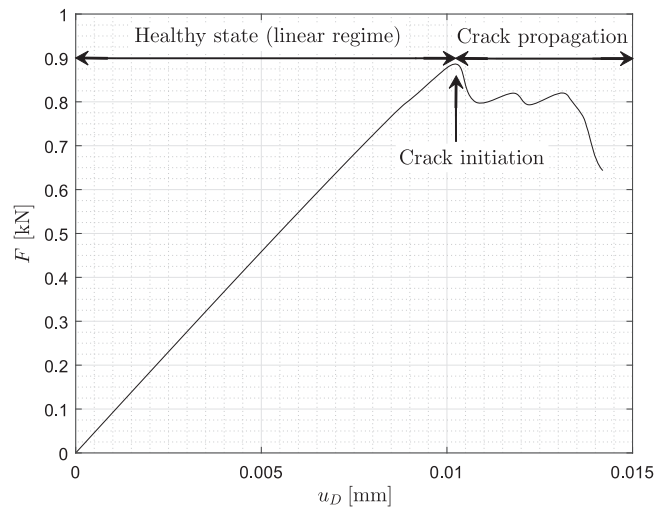


FIGURE 5 Simulated displacement-force response for the microstructure shown in the left panel in Figure 3

properties of the matrix are taken as $k_m = 175$ [GPa], $\mu_m = 81$ [GPa], and $g_{c,m} = 2.7 \times 10^{-3}$ [kN·mm⁻¹]. Dirichlet boundary conditions are applied in the form $\mathbf{u}_D(x_1, 0) = \mathbf{0}$ and $\mathbf{u}_D(x_1, L) = u_D \mathbf{e}^{(1)}$, for $0 \leq x_1 \leq L$, in which $\mathbf{e}^{(1)} = (1, 0)$ is the first vector of the canonical basis in $\mathbb{R}^2$ (note that $\partial\Omega_N = \emptyset$) and $u_D \in [0, \bar{u}_D]$ (see Figure 3). In the numerical results presented later, the value $u_D = 2 \times 10^{-5}$ [mm] is selected. An initial crack is positioned, as described in Figure 3. These boundary conditions correspond to a pure shear loading (see Figure 3), and the evolution of the damage field and displacement-force curve (associated with the microstructural sample shown in Figure 3) can be seen in Figures 4 and 5, for $\ell = 0.0075$ [mm] (in the two phases) and $\alpha = 10$. The finite element mesh adapted to this value of ℓ contains about 150 000 (linear

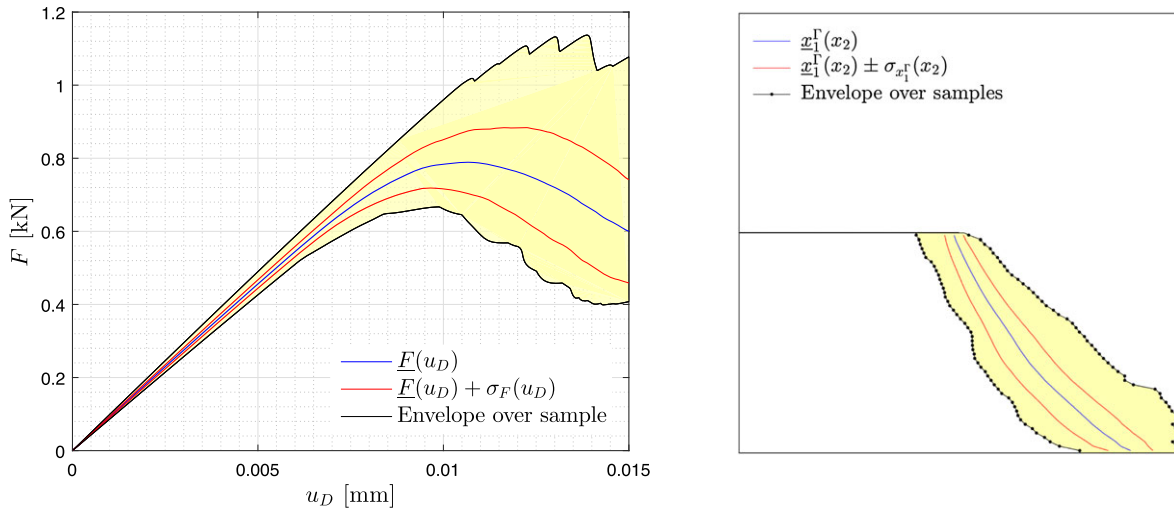


FIGURE 6 Envelope, mean, and standard deviation for the displacement-force curve (left) and the crack path (right)

triangular) elements, with a mesh size comprised between 3×10^{-4} and 1.5×10^{-2} [mm]. As expected, given the selected contrast in toughness, the crack exclusively propagates within the matrix phase. Since the crack path Γ is, by definition, identified as the collection of points $\mathbf{x}^\Gamma$ for which $d \approx 1$, and upon restricting the analysis to configurations containing a single crack, the variability in the crack propagation generated by the underlying microstructural randomness can be observed by considering the stochastic process $\{x_1^\Gamma(x_2), x_2 \in \mathbb{X}_2\}$, in which $\mathbb{X}_2 \subseteq [0, 0.5]$. Likewise, the stochasticity induced on the macroscopic response can be characterized by computing the horizontal force on the top edge ($x_2 = L$) of the samples, denoted by F . The mean and standard deviations for these quantities of interest, together with sample-based envelopes are shown in Figure 6. In these figures, $u_D \mapsto \underline{F}(u_D) = E\{F(u_D)\}$ and $u_D \mapsto \sigma_F(u_D) = \sqrt{E\{F(u_D)^2\} - E\{F(u_D)\}^2}$ represent the mean and variance functions for the macroscopic force, and the statistical estimators and envelopes are obtained using 100 independent realizations of the microstructure. Similar notations are used for studying the second-order properties of the process $\{x_1^\Gamma(x_2), x_2 \in \mathbb{X}_2\}$.

3 | STOCHASTIC MODELING OF CRACK PROPAGATION AT MESOSCALE

3.1 | Formulation for stochastic crack propagation at mesoscale

In this section, we propose a “simplified” model of crack propagation at a mesoscopic scale, where the piecewise constant fields of elastic properties defining the detailed microstructure are replaced by smoother approximations. In order to characterize crack propagation using coarse descriptors, we specifically introduce an *upscaled* version of the elasticity-phase-field problem as follows:

$$\begin{cases} \nabla \cdot [\sigma(\mathbf{u}, \mathbf{d})] = \mathbf{0}, \\ \frac{\tilde{g}_c}{\tilde{\ell}}(d - \tilde{\ell}^2 \Delta d) - 2(1 - d)\tilde{\Psi}^+([\epsilon]) = 0, \end{cases} \quad (13)$$

where the stress tensor

$$[\sigma(\mathbf{u}, \mathbf{d})] = (D(d) + \eta) \frac{\partial \tilde{\Psi}^+([\epsilon(\mathbf{u})])}{\partial [\epsilon(\mathbf{u})]} + \frac{\partial \tilde{\Psi}^-([\epsilon(\mathbf{u})])}{\partial [\epsilon(\mathbf{u})]} \quad (14)$$

is here expressed as a function of a new mesoscopic stored energy function

$$\tilde{\Psi}^\pm([\epsilon]) = [\epsilon^\pm] : [\tilde{\mathbb{C}}] : [\epsilon^\pm], \quad (15)$$

in which $\mathbf{x} \mapsto [\tilde{\mathbb{C}}(\mathbf{x})]$ is a mesoscopic elasticity tensor field, $\tilde{g}_c$ represents an equivalent toughness for the mesoscale medium, and $\tilde{\ell}$ is the characteristic length associated with the regularized description at the mesoscale. Note that (i) this mesoscale model differs from a fully homogenized one, as it maintains some statistical fluctuations raised by microstructural randomness; and (ii) the formulation remains predictive to study crack propagation, in contrast with an approach that would describe cracks through first-order averaged characteristics (such as crack density).

In what follows, the definition of the mesoscopic elasticity and equivalent toughness is investigated through the following two-step methodology.

- First, the definition of the elasticity field $\mathbf{x} \mapsto \llbracket \tilde{\mathbf{C}}(\mathbf{x}) \rrbracket$ is achieved using a moving-window upscaling approach under different types of boundary conditions. This point is discussed in Section 3.2.1.
- Second, the definition of the toughness $\tilde{g}_c$ is addressed in Section 3.2.2, where a statistical inverse problem involving the peak force at the macroscopic scale is introduced.

The results from the first step will be used, in Section 3.3, to construct a stochastic surrogate for the elasticity field. This model will enable us to draw additional samples of the mesoscopic elasticity field without having recourse to the homogenization solver.

3.2 | Definition of the mesoscopic coefficients

3.2.1 | Homogenization-based definition of mesoscopic elasticity tensor fields

In this section, we define the technique used to construct a mesoscopic (smooth) definition of the heterogeneous elastic medium from fully detailed realizations of microstructures. Such an approach has been extensively discussed over the past two decades. Within a multiscale setup, this can be achieved by using a local homogenization (see the work of Ostoja-Starzewski³² for a survey) or a filtering approach.^{33–35} For averaging-type upscaling, kinematic static uniform boundary conditions (KUBCs) and static uniform boundary conditions (SUBCs) (which are denoted by KUBC and SUBC hereinafter) can be considered³⁶ and provide bounds for the field of apparent tensors.^{37,38} Alternatively, PBCc can be invoked, especially when a fast convergence toward the effective properties is sought; PBC were employed in the so-called moving-window approach,³⁹ for instance. In the sequel, KUBCs and SUBCs are selected. While square-shaped domains are typically used in the literature of homogenization, a circular moving window is considered to prevent the generation of spurious anisotropic features at the mesoscale created by the corners of a square window (see, eg, the work of Bignonnet et al³⁴). A method using a moving window for obtaining a smoothed homogenized field with fluctuations is described in the following.

Let $\tilde{\Omega}_x$ be a circular domain of radius $\tilde{R}$, centered at $\mathbf{x} \in \Omega$, with boundary $\partial\tilde{\Omega}_x$. For one realization of the microstructure, $\{\llbracket \tilde{\mathbf{C}}(\mathbf{x}) \rrbracket, \mathbf{x} \in \Omega\}$ is obtained by performing a homogenization locally in $\tilde{\Omega}_x$, for both KUBC and SUBC (see Figure 7). As $\mathbf{x}$ moves within Ω , we obtain a continuous smooth homogenized medium characterized by a wavelength associated with radius $\tilde{R}$ (see illustrations of this process in Figure 10 for different radii $\tilde{R}$). We recall that KUBC correspond to the following boundary conditions:

$$\mathbf{u}_D^{(ij)}(\mathbf{z}) = [E^{(ij)}]\mathbf{z}, \quad \forall \mathbf{z} \in \partial\tilde{\Omega}_x, \quad (16)$$

where, in the present 2D plane strain context, indices i and j run over $\{1, 2\}$, leading to the following:

$$[E^{(11)}] = \begin{bmatrix} 1 & 0 \\ 0 & 0 \end{bmatrix}, \quad [E^{(22)}] = \begin{bmatrix} 0 & 0 \\ 0 & 1 \end{bmatrix}, \quad [E^{(12)}] = \frac{1}{2} \begin{bmatrix} 0 & 1 \\ 1 & 0 \end{bmatrix}. \quad (17)$$

The strategy is schematically depicted in Figure 7.

For SUBC, traction vectors are applied in the form

$$\mathbf{t}_N(\mathbf{z}) = [\Sigma^{(ij)}]\mathbf{n}(\mathbf{z}), \quad \forall \mathbf{z} \in \partial\tilde{\Omega}_x, \quad (18)$$

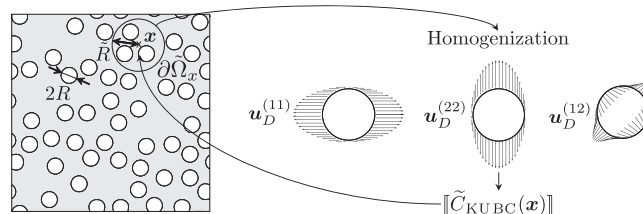


FIGURE 7 Defining mesoscale fields of stiffness through homogenization (case of kinematic uniform boundary condition)

where $\mathbf{n}(\mathbf{z})$ is the outward-pointing normal vector at point $\mathbf{z} \in \partial\tilde{\Omega}_{\mathbf{x}}$. Combinations of indices similar to those introduced for KUBC are considered, with

$$[\Sigma^{(11)}] = \begin{bmatrix} 1 & 0 \\ 0 & 0 \end{bmatrix}, \quad [\Sigma^{(22)}] = \begin{bmatrix} 0 & 0 \\ 0 & 1 \end{bmatrix}, \quad [\Sigma^{(12)}] = \frac{1}{2} \begin{bmatrix} 0 & 1 \\ 1 & 0 \end{bmatrix}. \quad (19)$$

Let $\{\tilde{\mathbf{C}}_{\text{KUBC}}(\mathbf{x}), \mathbf{x} \in \Omega\}$ and $\{\tilde{\mathbf{C}}_{\text{SUBC}}(\mathbf{x}), \mathbf{x} \in \Omega\}$ be the random fields of mesoscopic elasticity tensors defined under the aforementioned boundary conditions. Note that, when $\mathbf{x}$ approaches the boundary $\partial\Omega$, the realization of the microstructure is virtually replicated, by periodicity, and the mesoscopic tensor is still well defined.

Denoting by R the radius of the inclusions, ratio $\tilde{R}/R$ plays an important role in defining a continuous transition from the microscale ($\tilde{R}/R \rightarrow 0^+$) to the macroscale ($\tilde{R}/R \rightarrow +\infty$). Additionally, it specifies the level of anisotropy exhibited by the local apparent elasticity tensor, ranging from microscopic isotropy to mesoscopic anisotropy, and then to macroscopic isotropy (in the present case). This aspect turns out to be critical for the phase-field approach because the constitutive model used for the damaged material is based on the isotropy of the background media (see Section 3.1). In particular, the local isotropy of the underlying mesostructure is implicitly assumed in the presented formulation. The definition of the isotropic approximation for the mesoscale elasticity tensor field is addressed in the following.

Let $\{\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x}), \mathbf{x} \in \Omega\}$ denote the isotropic approximation of the field $\{\tilde{\mathbf{C}}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$, where the subscript “BC” refers to the type of boundary conditions under consideration (KUBC or SUBC). In 2D elasticity, and assuming plane strain conditions, the Voigt-type matrix representation $\{[\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x})], \mathbf{x} \in \Omega\}$ of the aforementioned field is given by

$$[\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x})] = \begin{bmatrix} \tilde{k}_{BC}(\mathbf{x}) + \frac{4}{3}\tilde{\mu}_{BC}(\mathbf{x}) & \tilde{k}_{BC}(\mathbf{x}) - \frac{2}{3}\tilde{\mu}_{BC}(\mathbf{x}) & 0 \\ \tilde{k}_{BC}(\mathbf{x}) - \frac{2}{3}\tilde{\mu}_{BC}(\mathbf{x}) & \tilde{k}_{BC}(\mathbf{x}) + \frac{4}{3}\tilde{\mu}_{BC}(\mathbf{x}) & 0 \\ 0 & 0 & \tilde{\mu}_{BC}(\mathbf{x}) \end{bmatrix}, \quad \forall \mathbf{x} \in \Omega, \quad (20)$$

where $\{\tilde{k}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ and $\{\tilde{\mu}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ are the random fields of 3d bulk and shear moduli defining the isotropic approximation, in plane strain elasticity, of the actual (anisotropic) elastic tensor $\tilde{\mathbf{C}}_{BC}(\mathbf{x})$. To obtain these coefficients, we minimize the distance (in the sense of the metric defined as follows) between $\tilde{\mathbf{C}}_{BC}(\mathbf{x})$ and $[\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x})]$ (see the works of Tran et al³⁵ and Guilleminot and Soize⁴⁰ and the references therein):

$$(\tilde{k}_{BC}(\mathbf{x}), \tilde{\mu}_{BC}(\mathbf{x})) = \underset{k>0, \mu>0}{\operatorname{argmin}} \left\| [\tilde{\mathbf{C}}_{BC}(\mathbf{x})] - [\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x})] \right\|_F^2, \quad (21)$$

in which

$$[\tilde{\mathbf{C}}_{BC}] = \begin{pmatrix} \tilde{C}_{11} & \tilde{C}_{12} & \tilde{C}_{13} \\ \tilde{C}_{12} & \tilde{C}_{22} & \tilde{C}_{23} \\ \tilde{C}_{13} & \tilde{C}_{23} & \tilde{C}_{33} \end{pmatrix}, \quad (22)$$

where Voigt's notation has been used for the different components of the tensor and $\|\cdot\|_F$ is the Frobenius norm.

The optimization problem defined by Equation (21) can readily be solved by a direct differentiation of the cost function, and the mesoscopic moduli of the isotropic approximation are found as

$$\tilde{k}(\mathbf{x}) = \frac{1}{60} (11\tilde{C}_{11}(\mathbf{x}) + 11\tilde{C}_{22}(\mathbf{x}) - 4\tilde{C}_{33}(\mathbf{x}) + 38\tilde{C}_{12}(\mathbf{x})), \quad \tilde{\mu}(\mathbf{x}) = \frac{1}{5} (\tilde{C}_{11}(\mathbf{x}) + \tilde{C}_{22}(\mathbf{x}) + \tilde{C}_{33}(\mathbf{x}) - 2\tilde{C}_{12}(\mathbf{x})), \quad (23)$$

where subscript “BC” has been dropped for notational convenience (this convention will be used in the sequel when no confusion is possible). In order to assess the relevance of the isotropic approximation, the following random field $\{\mathcal{A}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ is introduced^{35,40}:

$$\mathcal{A}_{BC}(\mathbf{x}) = \frac{\left\| [\tilde{\mathbf{C}}_{BC}(\mathbf{x})] - [\tilde{\mathbf{C}}_{BC}^{\text{iso}}(\mathbf{x})] \right\|_F}{\left\| [\tilde{\mathbf{C}}_{BC}(\mathbf{x})] \right\|_F}, \quad \forall \mathbf{x} \in \Omega. \quad (24)$$

The graphs of the fields of mean and standard deviation evaluated for a coarse mesoscopic grid (with 20 points along each direction) are shown in Figures 8 and 9, for both KUBC and SUBC.

It is seen that the error between the homogenization-based random fields and their isotropic approximations remain small in mean and variance, and that the error is larger in the case of KUBC. The effect of the mesoscopic resolution on the isotropic approximation (for KUBC) is qualitatively shown on a single realization in Figure 10. As expected, the field becomes more homogeneous as the ratio $\tilde{R}/R$ increases. The approximation in the set of isotropic tensors is satisfactory

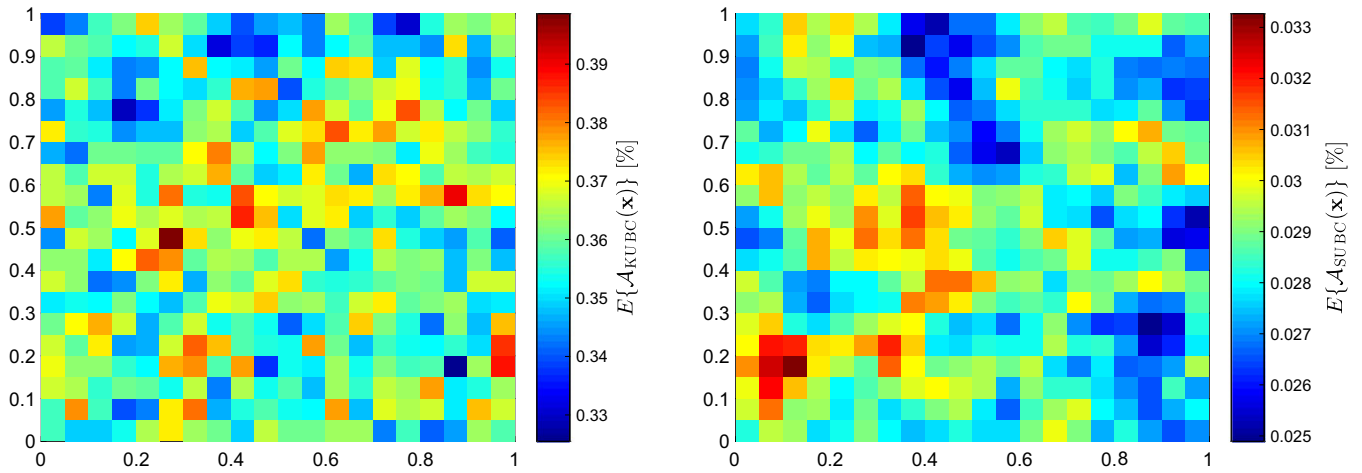


FIGURE 8 Graphs of the mean functions for the random fields $\{A_{KUBC}(x), x \in \Omega\}$ (left) and $\{A_{SUBC}(x), x \in \Omega\}$ (right). KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

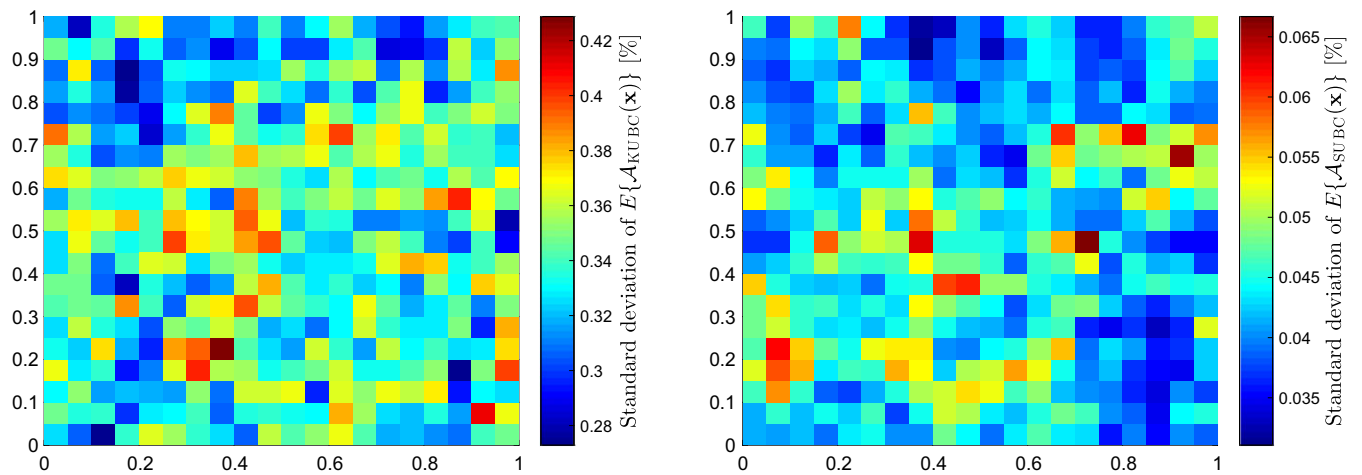


FIGURE 9 Graphs of the fields of standard deviation for the random fields $\{A_{KUBC}(x), x \in \Omega\}$ (left) and $\{A_{SUBC}(x), x \in \Omega\}$ (right). KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

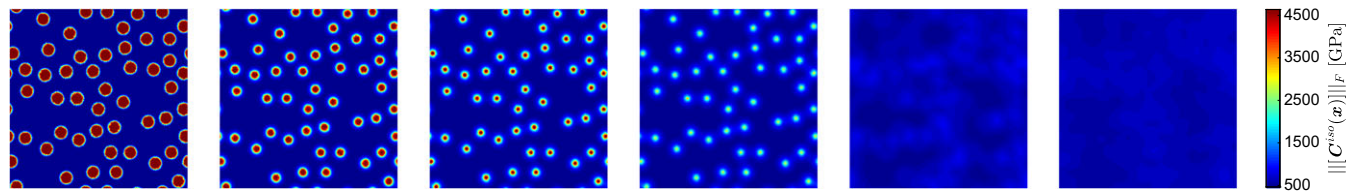


FIGURE 10 One realization of the random field $\{|||C^{iso}(x)|||_F, x \in \Omega\}$ for $\tilde{R}/R \in \{0.2, 0.6, 0.8, 1, 2, 4\}$ (from left to right)

and allows the phase-field approach to be readily applied in the isotropic case. In the rest of this paper, we will consider the characterization and simulation of the non-Gaussian fields $\{\tilde{k}_{BC}(x), x \in \Omega\}$ and $\{\tilde{\mu}_{BC}(x), x \in \Omega\}$ for $\tilde{R}/R = 3$.

The graphs of the first-order marginal probability density functions for the bulk and shear moduli are shown in Figure 11. The well-known ordering with respect to boundary conditions is observed almost surely (that is, $\tilde{k}_{SUBC} \leq \tilde{k}_{KUBC}$ and $\tilde{\mu}_{SUBC} \leq \tilde{\mu}_{KUBC}$ for each microstructural sample), and it is seen that the level of statistical fluctuations associated with KUBC is larger than for SUBC.

The estimated normalized correlation functions along $e^{(1)}$ and $e^{(2)}$ for the fields of bulk and shear moduli (for SUBC) are shown in Figure 12. In these figures, the notation $\tau_i \mapsto R_k^{data}(\tau_i)$ indicates that the correlation function of the bulk modulus random field is evaluated along the unit vector $e^{(i)}$ (a similar notation is used for the shear modulus). It is seen

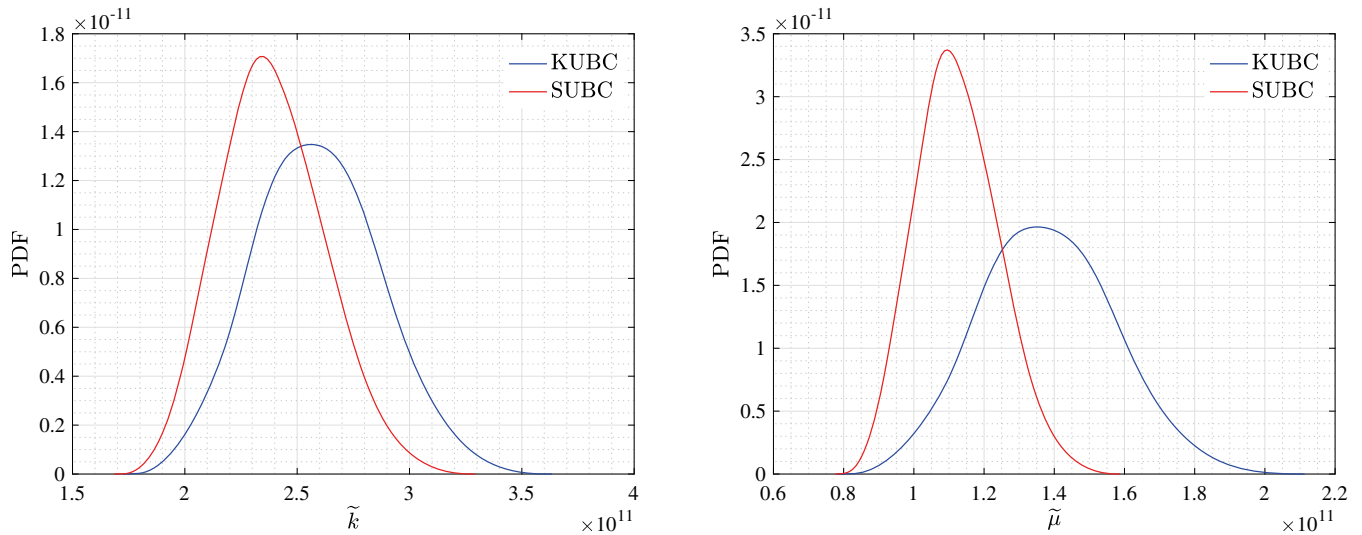


FIGURE 11 Graphs of the first-order marginal probability density functions for the bulk (left) and shear (right) moduli. KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

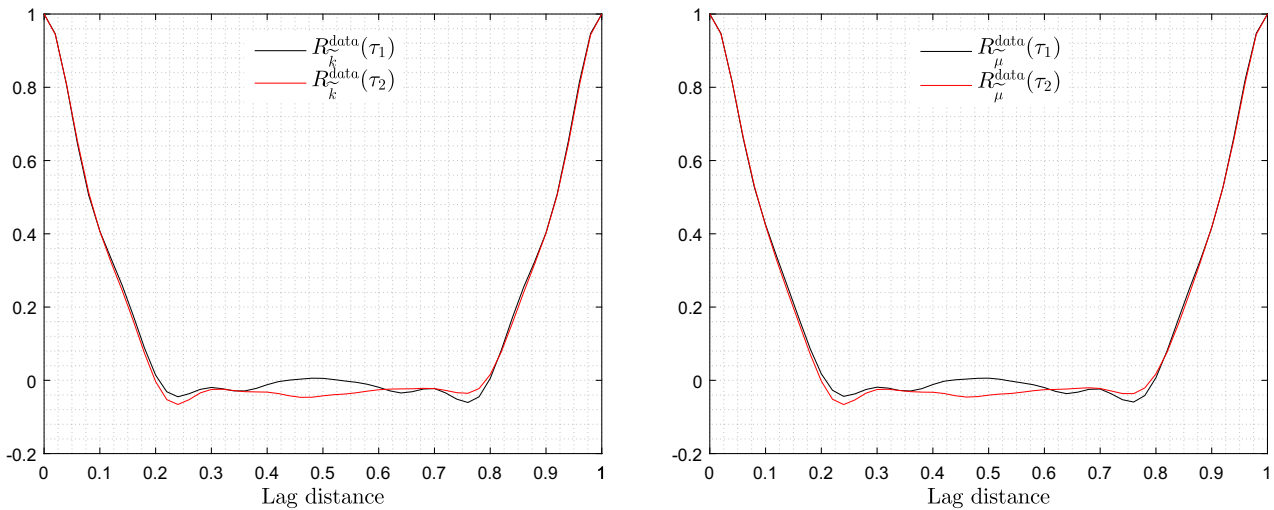


FIGURE 12 Graph of the correlation function along $\mathbf{e}^{(1)}$ and $\mathbf{e}^{(2)}$, estimated from the simulated data, for the random fields of bulk (left) and shear (right) moduli

that the differences between the correlation functions for the two random fields are almost indistinguishable, due to the very strong cross-correlation between the two properties. Moreover, it can be observed that the correlation first decreases over the range $[0, L/2]$ (with $L = 1$) and then starts increasing on $[L/2, L]$, in accordance with the periodicity of the underlying background medium. This information will be used to select an appropriate form of the correlation functions for the random field models, constructed in Section 3.3.1.

3.2.2 | Identification of the mesoscopic toughness

Let us now turn to the identification of the fracture and phase-field parameters $\tilde{g}_c$ and $\tilde{\ell}$ at the mesoscale (see Section 3.1). In this work, the characteristic length $\tilde{\ell}$ of the mesoscopic medium is set to be equal to the characteristic length at the microscale, previously denoted by ℓ , and $\tilde{g}_c$ is assumed constant. These choices are supported by a set of parametric studies, unreported hereinafter for the sake of conciseness, and by the numerical results presented in the work of Nguyen et al¹¹ for similar propagation regimes. It is worth noticing that, while the length scales are taken similar in both the microscopic and mesoscopic phase field equations (given by Equations (8) and (13) respectively), the mesh involved in the mesoscale description only needs to be refined in the vicinity of the crack. An adaptive meshing strategy can then be deployed to substantially reduce the computational cost (as opposed to the microscopic description in which the

mesh must be uniformly fine over the entire microstructure). The mesoscopic toughness parameter $\tilde{g}_c$ is next identified by solving an inverse problem involving the peak force $F_{\max} = \max_{u_D} F(u_D)$. More precisely, $\tilde{g}_c$ is calibrated by imposing a match between the mean value $\underline{F}_{\max}$ of $F_{\max}$, estimated with 500 independent microstructural samples and the fine-scale elasticity-phase-field simulations (detailed in Section 2.2), and the mean value determined with the mesoscopic description introduced in Section 3.1, denoted by $\tilde{F}_{\max}$. In the latter description, samples of the elasticity random field are estimated through the moving-window homogenization procedure, and the mesoscopic toughness then appears as the unique unknown parameter. Let $\tilde{F}_{\max}(\tilde{g}_c^*)$ be the mean peak force associated with the candidate value $\tilde{g}_c^*$ for the mesoscopic toughness (that is, by substituting $\tilde{g}_c^*$ for $\tilde{g}_c$ in Equation (13)). An optimal value can thus be defined by minimizing the relative error function

$$\mathcal{J}(\tilde{g}_c^*) = \frac{|F_{\max} - \tilde{F}_{\max}(\tilde{g}_c^*)|}{F_{\max}} \quad (25)$$

over the admissible set $[g_{c,m}, g_{c,i}]$

$$\tilde{g}_c = \underset{\tilde{g}_c^* \in [g_{c,m}, g_{c,i}]}{\operatorname{argmin}} \mathcal{J}(\tilde{g}_c^*). \quad (26)$$

Since the mesoscopic elasticity field depends on the boundary conditions applied, the aforementioned optimization problem must be solved independently for KUBC and SUBC. The graph of the cost function obtained for a resolution parameter $\alpha = 3$ is shown in the left panel in Figure 13. The optimal values are obtained as

$$\tilde{g}_c = 1.022 \times g_{c,m} \approx 2.75 \times 10^{-3} [\text{kN} \cdot \text{mm}^{-1}] \quad (27)$$

for KUBC and

$$\tilde{g}_c = 1.255 \times g_{c,m} \approx 3.375 \times 10^{-3} [\text{kN} \cdot \text{mm}^{-1}] \quad (28)$$

for SUBC. A comparison of the macroscopic responses obtained with the mesoscopic formulations (for KUBC and SUBC), parametrized with the identified values, and the reference computations is shown in the right panel in Figure 13; see also Figure 14 for a comparison of crack patterns. This figure shows that the mesoscale formulation identified under SUBC provides a fairly accurate estimate of the *mean* macroscopic response. This conclusion similarly holds for KUBC, although this type of boundary conditions leads to a stiffening of the response, in accordance with the fact that apparent tensors obtained under KUBC constitute upper bounds for the mesoscopic elasticity. In both cases, the variability is underestimated due to filtered elasticity fluctuations. These effects can clearly be observed in Figure 15, where the mean and standard deviation on crack paths are reported for the two types of boundary conditions. It is seen that the crack paths obtained with the mesoscopic formulations are localized near the mean crack path at microscale, for both KUBC and SUBC. Not surprisingly, the mesoscopic-based crack paths exhibit a variability that is much smaller than the one

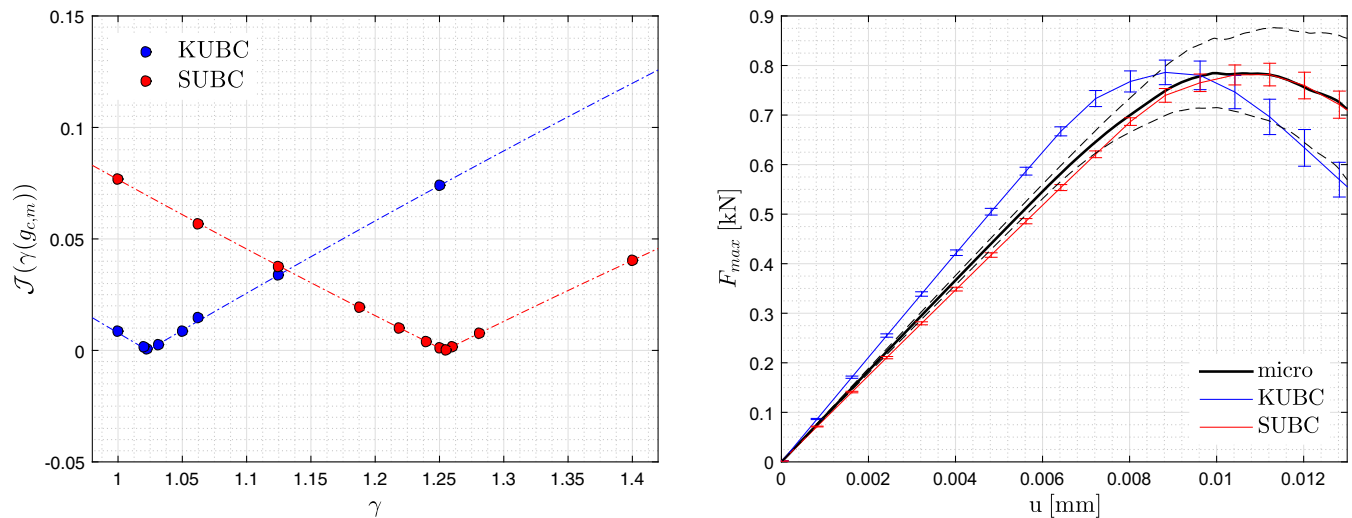


FIGURE 13 Graphs of the cost function for kinematic uniform boundary condition (KUBC) and static uniform boundary condition (SUBC) (left), and envelopes of the macroscopic response for the reference microscale model and the mesoscopic formulations (right)

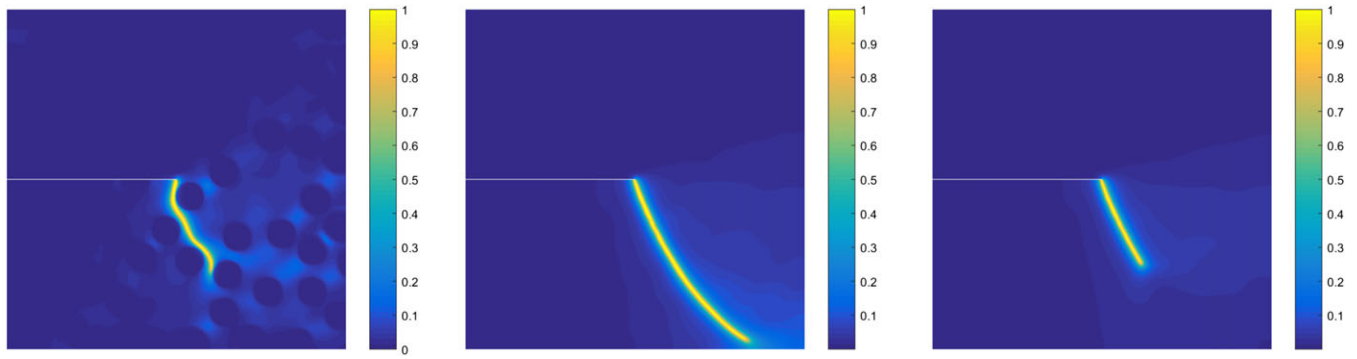


FIGURE 14 Crack path for the same microstructure: microscale description (left), KUBC-based description (middle), SUBC-based description (right). KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

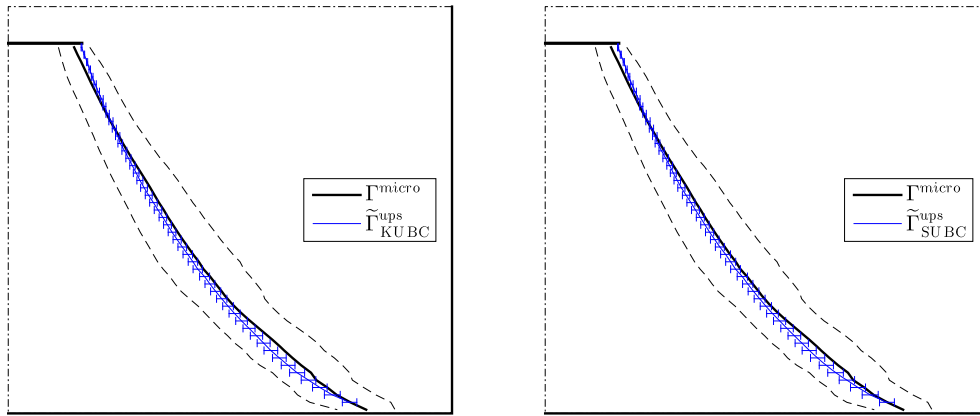


FIGURE 15 Comparison of crack paths obtained with the microscopic description (black dashed/solid lines) and the mesoscopic formulation. Left panel: case of KUBC. Right panel: case of SUBC. KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

obtained at microscale (where the crack trajectory is constrained by the radius of the inclusions). While the results support the relevance of the formulation, the latter necessitates solving a very large number of homogenization problems to represent the fluctuations of the elasticity field at the mesoscopic scale. In the next section, we address the construction of a stochastic model that enables the elasticity tensor random field to be sampled in a robust manner.

3.3 | Stochastic modeling and identification of mesoscale elasticity

3.3.1 | Construction of random field models

The construction of stochastic models for random fields of elasticity tensors with arbitrary material symmetries has been investigated in related works^{41–43} using an information-theoretic formulation⁴⁴ (see the work of Guilleminot and Soize et al⁴⁵ for a survey), and in the work of Malyarenko and Ostoj-Starzewski⁴⁶ using a spectral expansion. For a given type of boundary conditions, let $\{\tilde{k}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ and $\{\tilde{\mu}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ be the random fields of 3D bulk and shear moduli as defined in Equation (20).

Let $\{\Xi(\mathbf{x}) = (\Xi_1(\mathbf{x}), \Xi_2(\mathbf{x})), \mathbf{x} \in \Omega\}$ be a bivariate Gaussian field with statistically independent normalized components. These components are defined by the correlation functions $(\mathbf{x}, \mathbf{y}) \mapsto R_{\Xi_1}(\mathbf{x}, \mathbf{y}; \alpha^{(1)})$ and $(\mathbf{x}, \mathbf{y}) \mapsto R_{\Xi_2}(\mathbf{x}, \mathbf{y}; \alpha^{(2)})$. The non-Gaussian random fields of elastic moduli are then defined through the nonlinear transformations

$$\tilde{k}_{BC}(\mathbf{x}) = F_{G(p, q, \tilde{k})}^{-1}(F_{N(0,1)}(\Xi_1(\mathbf{x}))) \quad (29)$$

and

$$\tilde{\mu}_{BC}(\mathbf{x}) = F_{G(p, q, \tilde{\mu})}^{-1}\left(F_{N(0,1)}\left(\rho \Xi_1(\mathbf{x}) + \sqrt{1 - \rho^2} \Xi_2(\mathbf{x})\right)\right), \quad (30)$$

where $F_{G(p, q)}^{-1}$ is the inverse cumulative distribution function of the Gamma law with (shape and scale) parameters p and q (note that the dependence of these parameters on the boundary conditions is not reported for notational convenience),

$F_{N(0,1)}$ is the cumulative distribution function of the standard Gaussian law, and ρ denotes the correlation coefficient between $\tilde{k}_{BC}(\mathbf{x})$ and $\tilde{\mu}_{BC}(\mathbf{x})$.

Given the stationarity and the form of the correlation functions estimated for the random fields of elastic moduli (see Figure 12), the following separable form is retained:

$$R_{\Xi_i}(\mathbf{x}, \mathbf{y}; \boldsymbol{\alpha}^{(i)}) = r(\tau_1; \alpha_1^{(i)}) \times r(\tau_2; \alpha_2^{(i)}), \quad \forall \boldsymbol{\tau} \in ([0, L])^2, \quad i \in \{1, 2\}, \quad (31)$$

where $\tau_j = |\mathbf{x}_j - \mathbf{y}_j|$ is the lag distance along $\mathbf{e}^{(j)}$, $j \in \{1, 2\}$, and the 1D normalized correlation function $\tau \mapsto r(\tau; \alpha)$ is defined as

$$r(\tau; \alpha) = \exp\left(-\frac{2}{\alpha^2} \sin^2\left(\frac{\pi \tau}{L}\right)\right). \quad (32)$$

In Equation (32), α is a model parameter related to the internal length

$$\mathcal{L} = \int_0^{L/2} |r(\tau; \alpha)| d\tau, \quad (33)$$

which is interpreted, in the periodic setting under consideration, as the spatial correlation length of the Gaussian random field along the associated basis vector (eg, along $\mathbf{e}^{(1)}$ if the function $\tau_1 \mapsto r(\tau_1; \alpha_1^{(i)})$ is considered). It can be shown that the correlation length $\mathcal{L} < L/2$ reads as

$$\mathcal{L} = \frac{L}{2} \exp\{-\alpha^{-2}\} I_0(\alpha^{-2}), \quad (34)$$

where I_0 denotes the zero-order modified Bessel function. It should be noted that, by construction, one has $\mathcal{L}_i < L_i/2$. The graph of $\tau \mapsto r(\tau; \alpha)$ is shown in Figure 16 for different values of α .

The following properties can easily be deduced.

- The first-order marginal probability measure is a bivariate Gamma law,^{47,48} which is consistent with previous results derived within the framework of information theory (see the work of Guillemot and Soize⁴⁵ and the references therein).
- The mean values $\tilde{k}_{BC} = E\{\tilde{k}_{BC}(\mathbf{x})\}$ and $\tilde{\mu}_{BC} = E\{\tilde{\mu}_{BC}(\mathbf{x})\}$ read as

$$\tilde{k}_{BC} = p_{\tilde{k}} \times q_{\tilde{k}}, \quad \tilde{\mu}_{BC} = p_{\tilde{\mu}} \times q_{\tilde{\mu}}, \quad (35)$$

and the coefficients of variation are given as

$$\delta_{\tilde{k}_{BC}} = \frac{1}{\sqrt{p_{\tilde{k}}}}, \quad \delta_{\tilde{\mu}_{BC}} = \frac{1}{\sqrt{p_{\tilde{\mu}}}}. \quad (36)$$

Recall that these properties are independent of location $\mathbf{x}$, owing to the stationarity of the random fields.

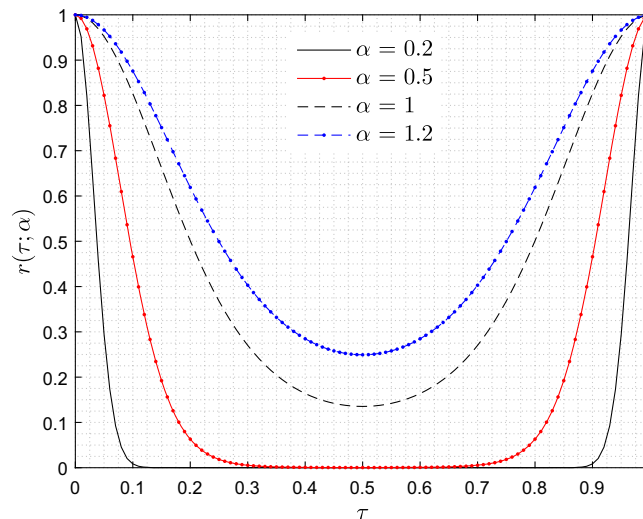


FIGURE 16 Plot of the correlation function $\tau \mapsto r(\tau; \alpha)$ for different values of α

- The fields of stiffness and compliance tensors are of second-order, ie,

$$E \left\{ \left\| \left[\tilde{C}_{BC}^{\text{iso}}(\mathbf{x}) \right] \right\|_F^2 \right\} < +\infty, \quad E \left\{ \left\| \left[\tilde{C}_{BC}^{\text{iso}}(\mathbf{x}) \right]^{-1} \right\|_F^2 \right\} < +\infty, \quad \forall \mathbf{x} \in \Omega, \quad (37)$$

hence ensuring that the stochastic linear elastic boundary value problem is well posed.⁴⁴

- The random fields $\{\tilde{k}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ and $\{\tilde{\mu}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ are mean-square continuous and mean-square differentiable.

From a computational standpoint, the underlying Gaussian fields are sampled using a truncated Karhunen-Loève expansion. In order to reduce the associated computation time, the random fields are sampled on a grid that is coarser than the one used to solve the elasticity-phase-field problem at the mesoscale. Realizations of fields are then obtained by interpolating on the fine mesoscopic grid. To that end, the coarse mesoscopic grid is specifically defined so that the correlation structure is properly discretized. In the results presented hereinafter, the coarse mesh includes six Gauss points per correlation length in each direction.

3.3.2 | Identification of the elasticity random field

The probabilistic model involves two sets of parameters controlling the joint probability density function of the elastic moduli at a given location and the correlation structure of the underlying Gaussian fields. The first set of parameters gathers $(p_{\tilde{k}}, q_{\tilde{k}})$ and $(p_{\tilde{\mu}}, q_{\tilde{\mu}})$ (or equivalently $(\tilde{k}_{BC}, \delta_{\tilde{k}_{BC}})$ and $(\tilde{\mu}_{BC}, \delta_{\tilde{\mu}_{BC}})$, in view of Equation (35)), as well as the coefficient of cross-correlation ρ . These hyperparameters can be estimated from the database using standard statistical estimators, here with 500 sample realizations, ie,

$$\tilde{k}_{\text{KUBC}} = 258.7 \text{ [GPa]}, \quad \delta_{\tilde{k}_{\text{KUBC}}} = 10.25\%, \quad \tilde{\mu}_{\text{KUBC}} = 137.7 \text{ [GPa]}, \quad \delta_{\tilde{\mu}_{\text{KUBC}}} = 13.30\%, \quad \rho = 0.9775, \quad (38)$$

$$\tilde{k}_{\text{SUBC}} = 238.6 \text{ [GPa]}, \quad \delta_{\tilde{k}_{\text{SUBC}}} = 9.3\%, \quad \tilde{\mu}_{\text{SUBC}} = 112.2 \text{ [GPa]}, \quad \delta_{\tilde{\mu}_{\text{SUBC}}} = 10\%, \quad \rho = 0.995. \quad (39)$$

The kernel density estimations of the first-order marginal and joint distribution for the bulk and shear moduli obtained with the data and the model-based samples are shown in Figures 17 and 18 (recall that the resolution is fixed by $\tilde{R}/R = 3$ here). A very good agreement is observed between the probability density functions corresponding to the homogenization-based data and those estimated with model-based samples. Since the transformations given by Equations (29) and (30) are nonlinear, the correlation functions associated with the random fields of elastic moduli cannot be inferred explicitly. In this case, the identification of the vector-valued hyperparameters $\alpha^{(1)}$ and $\alpha^{(2)}$ is performed through a two-step procedure, described later.

Let the correlation functions of $\{\tilde{k}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ and $\{\tilde{\mu}_{BC}(\mathbf{x}), \mathbf{x} \in \Omega\}$ be written as $\tau \mapsto R_{\tilde{k}}^{\text{model}}(\tau; \alpha^{(1)})$ and $\tau \mapsto R_{\tilde{\mu}}^{\text{model}}(\tau; (\alpha^{(1)}, \alpha^{(2)}))$, respectively; this notation emphasizes the underlying dependence on the parameters of the

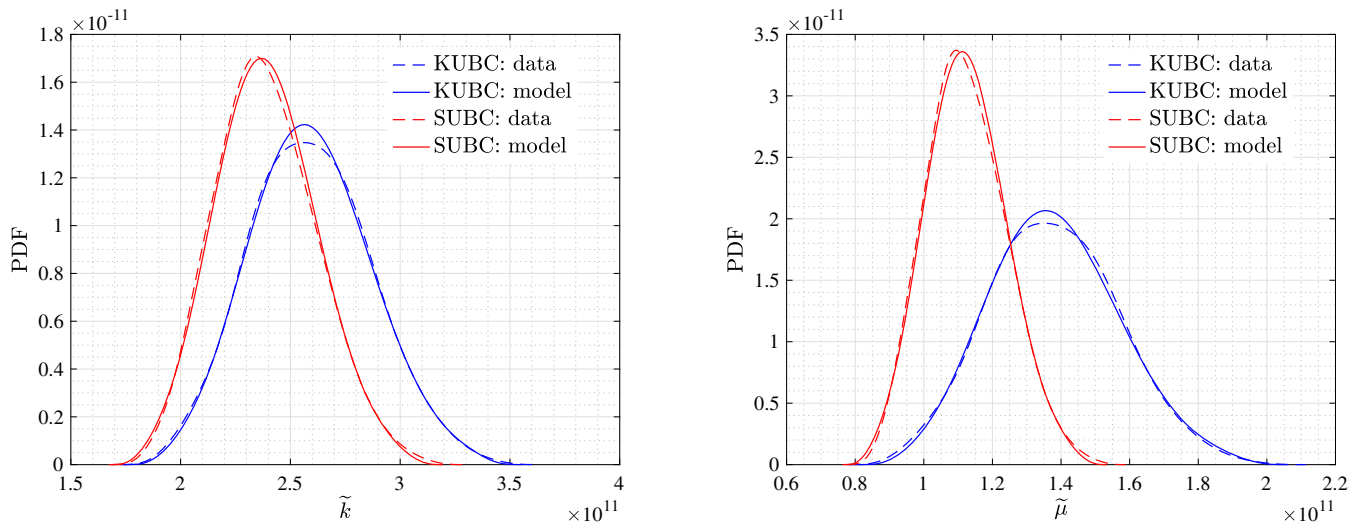


FIGURE 17 Kernel density estimates for the probability density function of the bulk (left) and shear (right) moduli, for the two types of boundary conditions kinematic uniform boundary condition (KUBC) (blue) and static uniform boundary condition (SUBC) (red)

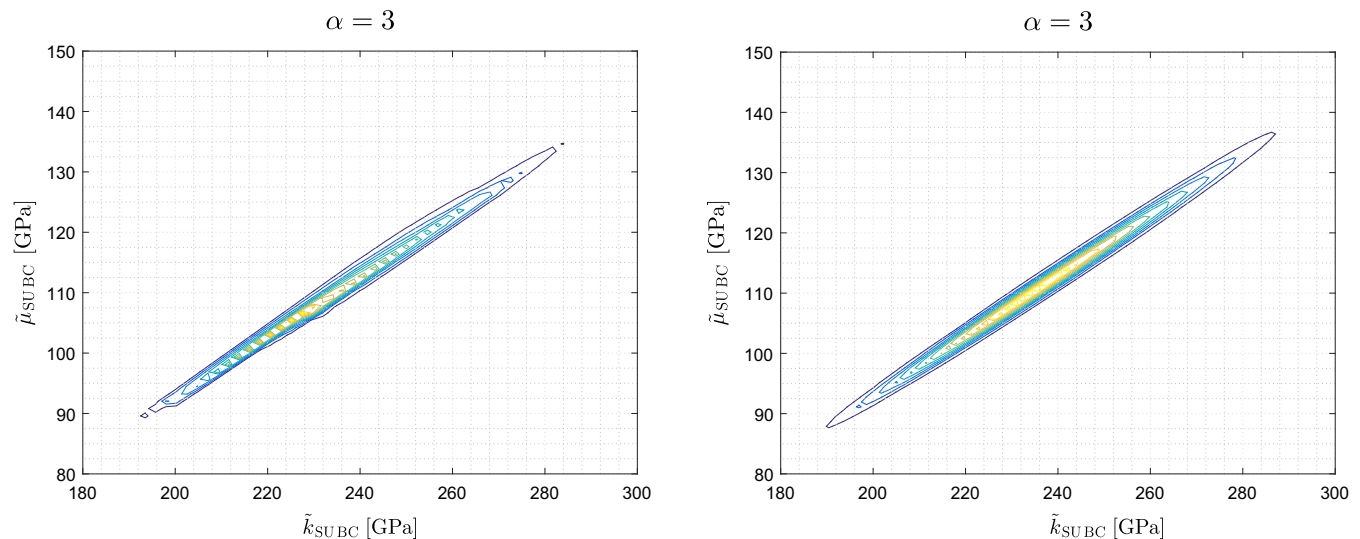


FIGURE 18 Kernel density estimates for the joint probability density function of the bulk and shear moduli, for homogenization-based (left) and model-based (right) samples (for SUBC). SUBC, static uniform boundary condition [Colour figure can be viewed at wileyonlinelibrary.com]

Gaussian fields (see Equations (29) and (30)). By a slight abuse of notation, these correlation functions will also be denoted as $\tau_j \mapsto R_{\tilde{k}}^{\text{model}}(\tau_j; \alpha_j^{(1)})$ and $\tau_j \mapsto R_{\tilde{\mu}}^{\text{model}}(\tau_j; (\alpha_j^{(1)}, \alpha_j^{(2)}))$ when evaluated along $\mathbf{e}^{(j)}$, $j \in \{1, 2\}$. In the first stage, the components of $\alpha^{(1)}$ are identified, for a given type of boundary conditions, as

$$\alpha_1^{(1)} = \underset{\alpha > 0}{\operatorname{argmin}} J_1^{(1)}(\alpha), \quad \alpha_2^{(1)} = \underset{\alpha > 0}{\operatorname{argmin}} J_2^{(1)}(\alpha), \quad (40)$$

where the cost functions are given by

$$J_1^{(1)}(\alpha) = \left(\int_0^{L/2} \left(R_{\tilde{k}}^{\text{data}}(\tau_1) - R_{\tilde{k}}^{\text{model}}(\tau_1; \alpha) \right)^2 d\tau_1 \right)^{1/2} \quad (41)$$

and

$$J_2^{(1)}(\alpha) = \left(\int_0^{L/2} \left(R_{\tilde{k}}^{\text{data}}(\tau_2) - R_{\tilde{k}}^{\text{model}}(\tau_2; \alpha) \right)^2 d\tau_2 \right)^{1/2}. \quad (42)$$

In the second stage, the hyperparameters controlling the correlation structure of the Gaussian random field $\{\Xi_2(\mathbf{x}), \mathbf{x} \in \Omega\}$ are identified as

$$\alpha_1^{(2)} = \underset{\alpha > 0}{\operatorname{argmin}} J_1^{(2)}(\alpha), \quad \alpha_2^{(2)} = \underset{\alpha > 0}{\operatorname{argmin}} J_2^{(2)}(\alpha), \quad (43)$$

in which

$$J_1^{(2)}(\alpha) = \left(\int_0^{L/2} \left(R_{\tilde{\mu}}^{\text{data}}(\tau_1) - R_{\tilde{\mu}}^{\text{model}}(\tau_1; (\alpha_1^{(1)}, \alpha)) \right)^2 d\tau_1 \right)^{1/2} \quad (44)$$

and

$$J_2^{(2)}(\alpha) = \left(\int_0^{L/2} \left(R_{\tilde{\mu}}^{\text{data}}(\tau_2) - R_{\tilde{\mu}}^{\text{model}}(\tau_2; (\alpha_2^{(1)}, \alpha)) \right)^2 d\tau_2 \right)^{1/2}. \quad (45)$$

In Equations (44) and (45), the values of $\alpha_1^{(1)}$ and $\alpha_2^{(1)}$ are those obtained within the first step of the methodology (see Equation (40)). In the following, the estimations of the correlation functions associated with the stochastic model are obtained. For given values of the hyperparameters, a set of 500 independent realizations of the random fields is first generated on a coarse grid with equidistant points. Usual statistical estimators are then used to estimate a set of correlation functions, indexed by the reference point (which is the point with respect to which the lag vector τ is defined).

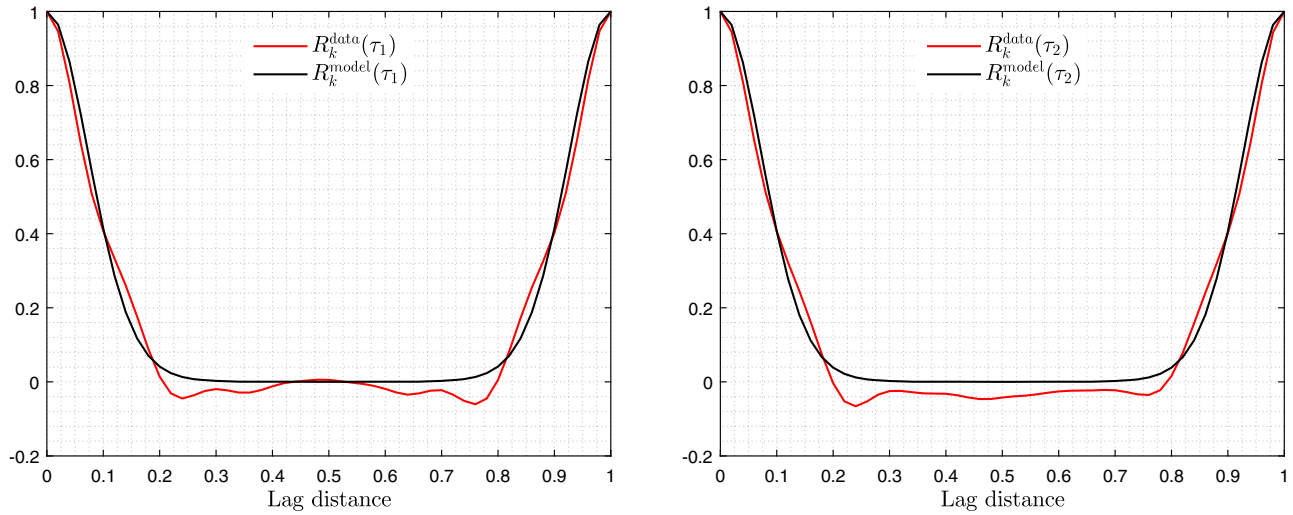


FIGURE 19 Normalized correlation function of the bulk modulus random field along $\mathbf{e}^{(1)}$ (left) and $\mathbf{e}^{(2)}$ (right), estimated from the multiscale data (red line) and the calibrated stochastic model (black line)

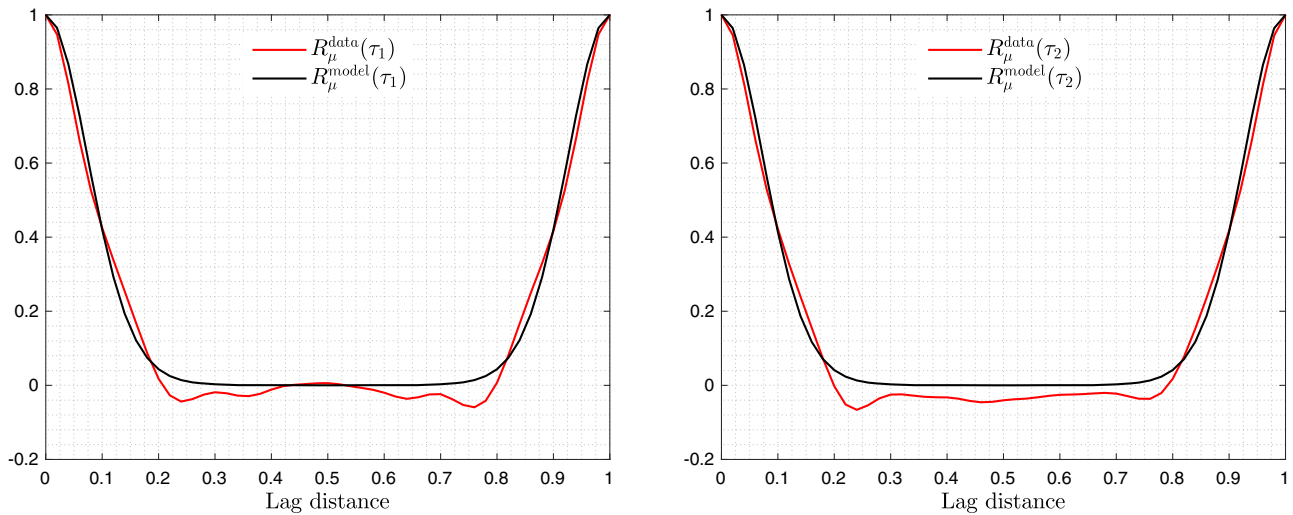


FIGURE 20 Normalized correlation function of the shear modulus random field along $\mathbf{e}^{(1)}$ (left) and $\mathbf{e}^{(2)}$ (right), estimated from the multiscale data (red line) and the calibrated stochastic model (black line)

Spatial averaging over properly selected reference points is finally applied to improve the quality of the estimations. The optimal values are found as

$$\boldsymbol{\alpha}^{(1)} = (0.4624, 0.4574), \quad \boldsymbol{\alpha}^{(2)} = (0.4043, 0.4014) \quad (46)$$

for the elasticity random fields identified under KUBC, and

$$\boldsymbol{\alpha}^{(1)} = (0.4654, 0.4604), \quad \boldsymbol{\alpha}^{(2)} = (0.4694, 0.4654) \quad (47)$$

for the case of SUBC. The graphs of the normalized correlation functions estimated with the data and with the stochastic model thus identified (under SUBC) are shown in Figures 19 and 20 for the bulk and shear moduli random fields, respectively. It is seen that the calibrated model allows the decays of the correlation functions to be accurately reproduced, which is key to mimicking the mesoscopic elasticity (and, in particular, the frequency of sample path oscillations that has a substantial impact on the crack paths in the phase-field formulation at mesoscale).

3.4 | Comparison Between the microscopic and mesoscopic formulations

The variability in crack paths can be observed in Figure 21 for the reference microscale-based computations and the mesoscopic formulation defined with either locally-homogenized microstructural samples (following the approach detailed in

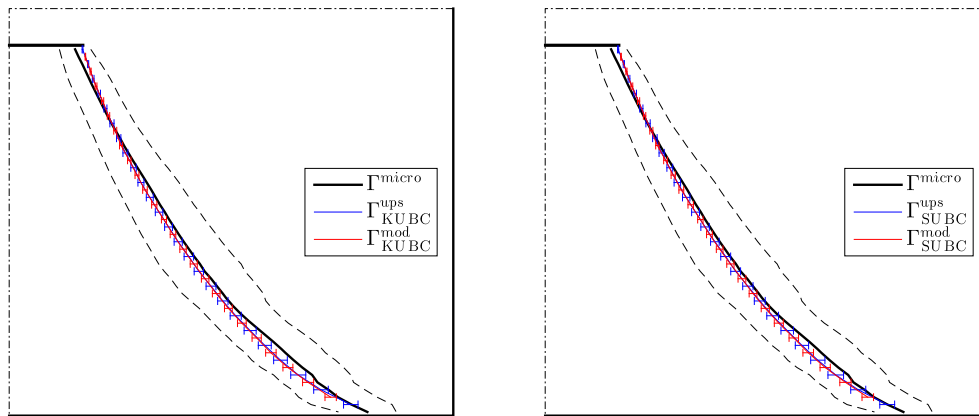


FIGURE 21 Comparison of crack paths obtained with the microscopic description (black dashed/solid lines), the mesoscopic formulation where the elasticity is obtained from microstructural samples (blue lines), and the mesoscopic formulation involving the stochastic model for elasticity tensors (red lines). Left panel: case of KUBC. Right panel: case of SUBC. KUBC, kinematic uniform boundary condition; SUBC, static uniform boundary condition

Section 3.2.1) or the elasticity field stochastic model. It can be observed that the crack paths corresponding to a description at microscale present larger statistical fluctuations. As previously indicated, this result is indeed expected because the propagation only occurs in the matrix phase then (hence, forcing the crack to get around inclusions). In contrast, the mesoscopic formulations exhibit much smaller variability but capture quite accurately the mean crack path. Interestingly, it is seen that the stochastic model for the elasticity tensor random field performs well in delivering crack paths that are consistent with those computed with homogenization-based fields.

The predictions of the macroscopic force-displacement curve are shown in Figure 22. In accordance with the results presented in Section 3.2.2 (see the right panel in Figure 13), where microscopic and homogenization-based mesoscopic formulations were compared, it is observed that the mesoscopic elasticity-phase-field formulation defined under SUBC delivers predictions in better agreement with the reference solution, in terms of both the mean elastic response and mean peak force. In contrast, the use of KUBC at the mesoscale generates a stiffer response in the elastic regime while still allowing for a good prediction of the mean peak force. In addition, the use of the stochastic model in lieu of homogenization-based samples does not introduce any significant bias in the predictions, regardless of the type of boundary conditions. Upon interpreting the macroscopic force as a stochastic process indexed by the prescribed displacement,

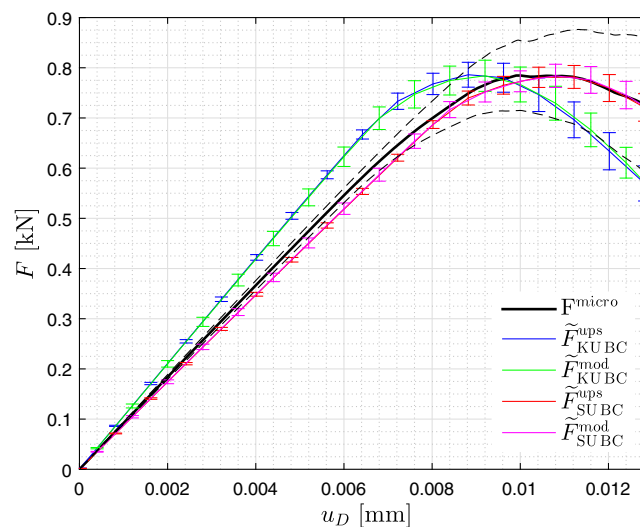


FIGURE 22 Envelopes of the macroscopic response for the reference microscale model (F) and the mesoscopic formulations parametrized either by upscaled coefficients ($\tilde{F}_{\text{KUBC}}^{\text{ups}}$, $\tilde{F}_{\text{SUBC}}^{\text{ups}}$) or model-based coefficients ($\tilde{F}_{\text{KUBC}}^{\text{mod}}$, $\tilde{F}_{\text{SUBC}}^{\text{mod}}$)

the error generated by the proposed model-based, mesoscopic formulation can be characterized as

$$\varepsilon = \frac{\left| E \left\{ \int_0^{\bar{u}_D} F(u_D)^2 du_D \right\}^{1/2} - E \left\{ \int_0^{\bar{u}_D} \tilde{F}(u_D)^2 du_D \right\}^{1/2} \right|}{E \left\{ \int_0^{\bar{u}_D} F(u_D)^2 du_D \right\}^{1/2}}, \quad (48)$$

where the stochastic process $\{\tilde{F}(u_D), u_D \in [0, \bar{u}_D]\}$ is implicitly depending on the boundary conditions applied at mesoscale. The right-hand side term in Equation (48) can be estimated through Monte Carlo simulations, and the relative error remains small for the two types of boundary conditions, with $\varepsilon \approx 1.6\%$ for KUBC and $\varepsilon \approx 2.2\%$ for SUBC. The error for the prediction of the mean peak force can be characterized by

$$\varepsilon_{\max} = \left| \frac{F_{\max} - \tilde{F}_{\max}}{F_{\max}} \right|. \quad (49)$$

The error measure is given by $\varepsilon_{\max} \approx 0.084\%$ for KUBC and $\varepsilon_{\max} \approx 0.037\%$ for SUBC, showing that an accurate prediction of the mean peak force can be obtained with the two types of boundary conditions. Finally, the fact that the mesoscopic approach underestimates the variability in the macroscopic response is expected, given the nature of the propagation at microscale. In this context, the deviation from the mean crack path is more contained than in the microscopic simulations where the crack essentially propagates around the heterogeneities. Depending on the application of interest, one possible way to compensate for this intrinsic effect could be to adopt a goal-oriented strategy, where (fictitious) anisotropic fluctuations are incorporated into the mesoscopic elasticity field (by means of a generalized stochastic model; see the works of Guillemot and Soize^{41,49}), and where the hyperparameters of the stochastic model are calibrated by solving a statistical inverse problem on the macroscopic response (using an appropriate identification metric that is sensitive to both the mean and variance along the macroscopic loading path).

4 | CONCLUSION

A stochastic approach to model crack propagation in random media has been proposed in this paper. The formulation relies on a phase-field formulation, where material coefficients are defined and identified through multiscale computations. Monte-Carlo simulations were first performed using a description at the microscopic scale. These computations enables the characterization of subscale-induced randomness on the macroscopic response of the domain and were subsequently used as reference results to assess the relevance of the framework. The definition of the mesoscopic parameters was then addressed. The elasticity field at mesoscale was specifically defined as the isotropic approximation of spatially dependent homogenized tensors, obtained by means of a moving-window upscaling approach (under kinematically and statically uniform boundary conditions). The (deterministic) mesoscopic toughness was identified by solving an inverse problem related to the mean peak force. It is shown that the formulation under statically uniform boundary conditions allows for an accurate prediction of the mean elastic response and mean peak force. In contrast, kinematically uniform boundary conditions generate a stiffening of mesoscale elasticity, in accordance with theoretical results derived elsewhere. An information-theoretical probabilistic model for the elasticity random field was then constructed and allows for a fast robust sampling of mesoscopic elasticity. The results obtained by feeding this stochastic surrogate model into the phase-field formulation were finally compared with those corresponding to the full-scale microscopic model. It is shown, in particular, that the model-based mesoscopic elasticity-phase-field formulation associated with statically uniform boundary conditions allows for an accurate prediction of both the mean elastic response and mean peak force. Various extensions of the proposed framework are envisioned to address other types of propagation regimes (eg, when the crack does not only propagate within the matrix phase at microscale) and to refine the way the statistical fluctuations are accounted for at the mesoscopic scale. Such generalizations could be achieved by tailoring the nature and structure of the fields parameterizing the elasticity-phase-field formulation by considering more sophisticated structures of anisotropic fluctuations and a spatially dependent toughness field for instance and by adapting the identification strategy based on intended purpose. Such extensions are much beyond the scope of the proposed study and constitute interesting directions for future work.

ORCID

Johann Guillemot  <https://orcid.org/0000-0003-3738-4370>

Julien Yvonnet  <https://orcid.org/0000-0002-9365-6601>

REFERENCES

- Kulkarni MG, Matouš K, Geubelle PH. Coupled multiscale cohesive modeling of failure in heterogeneous adhesives. *Int J Numer Methods Eng*. 2010;84(8):916-946.
- Nguyen VP, Lloberas-Valls O, Stroeve M, Sluys LJ. Homogenization-based multiscale crack modelling: from micro-diffusive damage to macro-cracks. *Comput Methods Appl Mech Eng*. 2011;200(9-12):1220-1236.
- Loehnert S, Belytschko T. A multiscale projection method for macro/microcrack simulations. *Int J Numer Methods Eng*. 2007;71(12):1466-1482.
- Liu G, Zhou D, Bao Y, Ma J, Han Z. Multiscale simulation of major crack/minor cracks interplay with the corrected XFEM. *Arch Civ Mech Eng*. 2017;17(2):410-418.
- Coenen EWC, Kouznetsova VG, Bosco E, Geers MGD. A multi-scale approach to bridge microscale damage and macroscale failure: a nested computational homogenization-localization framework. *Int J Fract*. 2012;178(1-2):157-178.
- Oliver J, Caicedo M, Roubin E, Huespe AE, Hernández JA. Continuum approach to computational multiscale modeling of propagating fracture. *Comput Methods Appl Mech Eng*. 2015;294:384-427.
- Rudoy E. Domain decomposition method for crack problems with nonpenetration condition. *ESAIM Math Model Numer Anal*. 2016;50:995-1009.
- Teichtmeister S, Kienle D, Aldakheel F, Keip M-A. Phase field modeling of fracture in anisotropic brittle solids. *Int J Non-Linear Mech*. 2017;97:1-21.
- Waisman H, Berger-Vergat L. An adaptive domain decomposition preconditioner for crack propagation problems modeled by XFEM. *Int J Multiscale Comput Eng*. 2013;11(6):633-654.
- Hossain MZ, Hsueh C-J, Bourdin B, Bhattacharya K. Effective toughness of heterogeneous media. *J Mech Phys Solids*. 2014;71:15-32.
- Nguyen N, Yvonnet J, Réthoré J, Tran AB. Identification of fracture models based on phase field for crack propagation in heterogeneous lattices in a context of non-separated scales. *Computational Mechanics*. 2019;63(5):1047-1068.
- Bazant ZP, Planas J. *Fracture and Size Effect in Concrete and Other Quasibrittle Materials*. Boca Raton, FL: CRC Press; 1998.
- Bazant ZP, Novák D. Probabilistic nonlocal theory for quasibrittle fracture initiation and size effect. I: theory. *J Eng Mech*. 2000;126(2):166-174.
- van Vliet MRA, van Mier JGM. Experimental investigation of size effect in concrete and sandstone under uniaxial tension. *Eng Fract Mech*. 2000;65(2-3):165-188.
- Genet M, Couégnat G, Tomsia AP, Ritchie RO. Scaling strength distributions in quasi-brittle materials from micro- to macro-scales: a computational approach to modeling nature-inspired structural ceramics. *J Mech Phys Solids*. 2014;68:93-106.
- Tregger N, Corr D, Graham-Brady L, Shah S. Modeling the effect of mesoscale randomness on concrete fracture. *Probabilistic Eng Mech*. 2006;21(3):217-225.
- Daphalapurkar NP, Ramesh KT, Graham-Brady L, Molinari J-F. Predicting variability in the dynamic failure strength of brittle materials considering pre-existing flaws. *J Mech Phys Solids*. 2011;59(2):297-319.
- Rahman S, Chakraborty A. Stochastic multiscale fracture analysis of three-dimensional functionally graded composites. *Eng Fract Mech*. 2011;78(1):27-46.
- Acton KA, Baxter SC, Bahmani B, Clarke PL, Abedi R. Voronoi tessellation based statistical volume element characterization for use in fracture modeling. *Comput Methods Appl Mech Eng*. 2018;336:135-155.
- Francfort GA, Marigo J-J. Revisiting brittle fracture as an energy minimization problem. *J Mech Phys Solids*. 1998;46(8):1319-1342.
- Bourdin B, Francfort GA, Marigo J-J. Numerical experiments in revisited brittle fracture. *J Mech Phys Solids*. 2000;48(4):797-826.
- Bourdin B, Francfort GA, Marigo J-J. The variational approach to fracture. *J Elast*. 2008;91(1-3):5-148.
- Miehe C, Hofacker M, Welschinger F. A phase field model for rate-independent crack propagation: robust algorithmic implementation based on operator splits. *Comput Methods Appl Mech Eng*. 2010;199:2765-2778.
- Mumford D, Shah J. Optimal approximations by piecewise smooth functions and associated variational problems. *Commun Pure Appl Math*. 1989;42(5):577-685.
- Ambrosio L, Tortorelli VM. Approximation of functional depending on jumps by elliptic functional via t-convergence. *Commun Pure Appl Math*. 1990;43(8):999-1036.
- Borden MJ, Hughes TJR, Landis CM, Verhoosel CV. A higher-order phase-field model for brittle fracture: formulation and analysis within the isogeometric analysis framework. *Comput Methods Appl Mech Eng*. 2014;273:100-118.
- Amor H, Marigo J-J, Maurini C. Regularized formulation of the variational brittle fracture with unilateral contact: numerical experiments. *J Mech Phys Solids*. 2009;57(8):1209-1229.
- Pham K, Marigo J-J, Maurini C. The issues of the uniqueness and the stability of the homogeneous response in uniaxial tests with gradient damage models. *J Mech Phys Solids*. 2011;59(6):1163-1190.
- Nguyen TT, Yvonnet J, Bornert M, et al. On the choice of parameters in the phase field method for simulating crack initiation with experimental validation. *Int J Fract*. 2016;197(2):213-226.
- Kuhn C, Schlüter A, Müller R. On degradation functions in phase field fracture models. *Comput Mater Sci*. 2015;108:374-384.
- Zamponi F. Comment on "packing hyperspheres in high-dimensional Euclidean spaces". *Phys Rev E*. 2007;75(4).
- Ostoja-Starzewski M. *Microstructural Randomness and Scaling in Mechanics of Materials*. New York, NY: Chapman and Hall/CRC; 2007.
- Yvonnet J, Bonnet G. A consistent nonlocal scheme based on filters for the homogenization of heterogeneous linear materials with non-separated scales. *Int J Solids Struct*. 2014;51(1):196-209.

34. Bignonnet F, Sab K, Dormieux L, Brisard S, Bisson A. Macroscopically consistent non-local modeling of heterogeneous media. *Comput Methods Appl Mech Eng*. 2014;278:218-238.
35. Tran VP, Guilleminot J, Brisard S, Sab K. Stochastic modeling of mesoscopic elasticity random field. *Mech Mater*. 2016;93:1-12.
36. Ostoja-Starzewski M. Random field models of heterogeneous materials. *Int J Solids Struct*. 1998;35(19):2429-2455.
37. Huet C. Application of variational concepts to size effects in elastic heterogeneous bodies. *J Mech Phys Solids*. 1990;38(6):813-841.
38. Hazanov S, Huet C. Order relationships for boundary condition effect in heterogeneous bodies smaller than the representative volume. *J Mech Phys Solids*. 1994;42(12):1995-2011.
39. Graham LL, Gurley K, Masters F. Non-Gaussian simulation of local material properties based on a moving-window technique. *Probabilistic Eng Mech*. 2003;18(3):223-234.
40. Guilleminot J, Soize C. Stochastic modeling of anisotropy in multiscale analysis of heterogeneous materials: a comprehensive overview on random matrix approaches. *Mech Mater*. 2012;44:35-46.
41. Guilleminot J, Soize C. Stochastic model and generator for random fields with symmetry properties: application to the mesoscopic modeling of elastic random media. *Multiscale Model Simul*. 2013;11:840-870.
42. Guilleminot J, Soize C. On the statistical dependence for the components of random elasticity tensors exhibiting material symmetry properties. *J Elast*. 2013;111:109-130.
43. Staber B, Guilleminot J. Stochastic modeling and generation of random fields of elasticity tensors: a unified information-theoretic approach. *Comptes Rendus Mécanique*. 2017;345(6):399-416.
44. Soize C. Non-Gaussian positive-definite matrix-valued random fields for elliptic stochastic partial derivative operators. *Comput Meth Appl Mech Eng*. 2006;195:26-64.
45. Guilleminot J, Soize C. Non-Gaussian random fields in multiscale mechanics of heterogeneous materials. In: *Encyclopedia of Continuum Mechanics*. Berlin, Germany: Springer Berlin Heidelberg; 2017:1-9.
46. Malyarenko A, Ostoja-Starzewski M. A random field formulation of Hooke's law in all elasticity classes. *J Elast*. 2017;127(2):269-302.
47. Moran P. Statistical inference with bivariate gamma distributions. *Biometrika*. 1969;56:627-634.
48. Arnst M, Ponthot J-P. An overview of nonintrusive characterization, propagation, and sensitivity analysis of uncertainties in computational mechanics. *Int J Uncertain Quantif*. 2014;4(5):387-421.
49. Guilleminot J, Soize C. Generalized stochastic approach for constitutive equation in linear elasticity: a random matrix model. *Int J Numer Methods Eng*. 2012;90(5):613-635.

How to cite this article: Hun D-A, Guilleminot J, Yvonnet J, Bornert M. Stochastic multiscale modeling of crack propagation in random heterogeneous media. *Int J Numer Methods Eng*. 2019;119:1325-1344. <https://doi.org/10.1002/nme.6093>